SAND2009-0125C

Peridynamic Modeling of the Dynamic Response of Heterogeneous Media

Stewart Silling, Richard Lehoucq
Sandia National Laboratories

Abe Askari, Olaf Weckner
The Boeing Company

Florin Bobaru
University of Nebraska, Lincoln

Minisymposium on
Nonlocal and Scale Effects in Dynamic Shear Banding or in Dynamic Damage of Heterogeneous Media

International Symposium on Plasticity

January 6, 2009

Sandia is a multiprogram laboratory operated by Sandia Corporation, a Lockheed Martin Company, for the United States Department of Energy under contract DE-AC04-94AL85000.

Sandia National Laboratories

Outline

- Objective
- Theory
- EMU numerical method
- Examples
- Heterogeneity and nonlocality
- Fragmentation

Sandia National Laboratories

Purposes of the peridynamic model

- To be able to apply the same equations on or off of cracks.
- To treat discrete particles using the same equations as continua.

- Why do this?
  - The standard theory is not a good tool for modeling cracks.
    - PDEs do not apply on discontinuities or to discrete particles.
    - This leads to the need for special techniques when cracks are present.
  - No natural way to couple atoms to continua.

Sandia National Laboratories

Strategy

Replace the standard PDEs with integral equations.

- The integral equations involve interaction between points separated by finite distances (nonlocality).
- The integral equations are not derivable from the PDEs.
  - But they converge to the PDEs in the limit of small length scales.

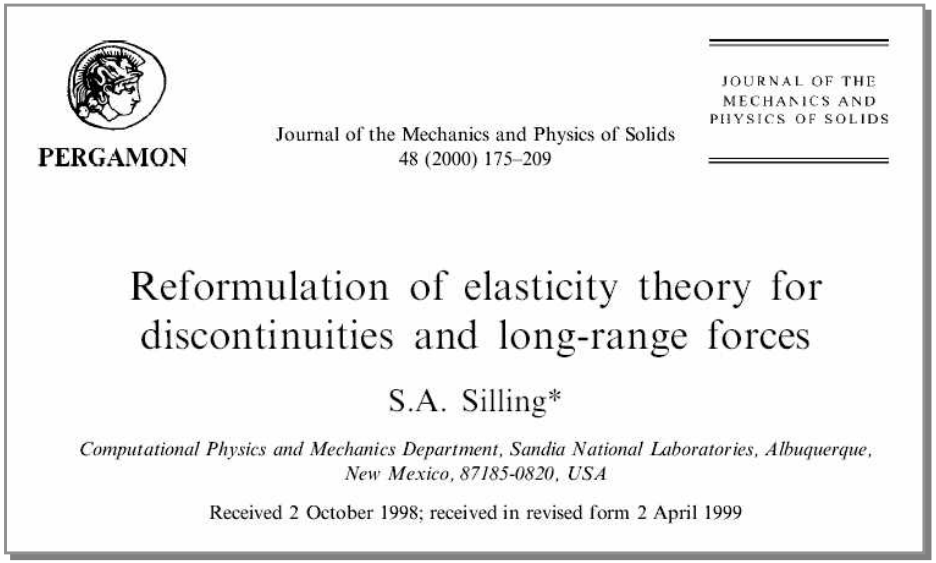

PERGAMON

Journal of the Mechanics and Physics of Solids
48 (2000) 175–209

JOURNAL OF THE MECHANICS AND PHYSICS OF SOLIDS

Reformulation of elasticity theory for discontinuities and long-range forces

S.A. Silling*

Computational Physics and Mechanics Department, Sandia National Laboratories, Albuquerque, New Mexico, 87185-0820, USA

Received 2 October 1998; received in revised form 2 April 1999

Sandia National Laboratories

Outline

- Objective
- Theory
- EMU numerical method
- Examples
- Heterogeneity and nonlocality
- Fragmentation

Sandia National Laboratories

The basic assumption

The strain energy density at any point $\mathbf{x}$ depends on the deformation of a neighborhood $\mathcal{H}$ of $\mathbf{x}$.

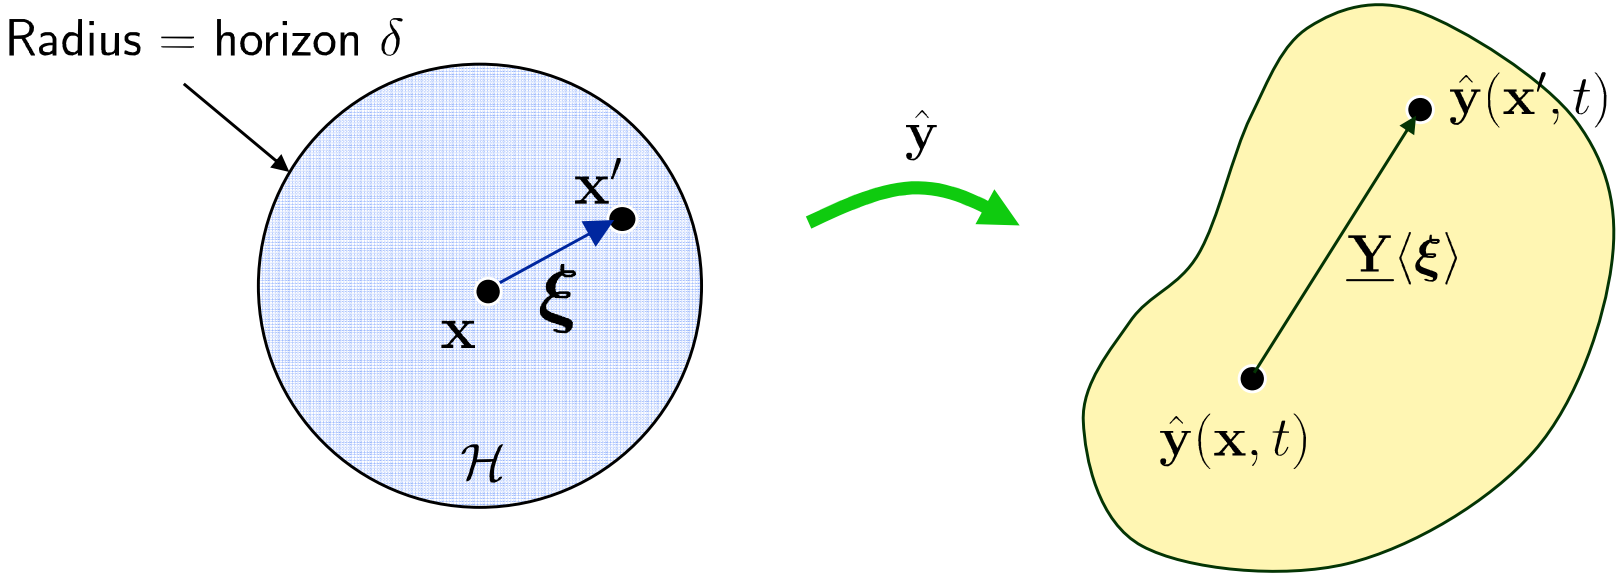

Undeformed family of $\mathbf{x}$ Deformed family of $\mathbf{x}$

Now need to introduce some tools ("peridynamic states") for keeping track of how these neighborhoods deform.

Sandia National Laboratories

Peridynamic states: Mathematical tool for dealing with collections of bonds

A peridynamic vector state $\underline{\mathbf{A}}$ is a mapping from $\mathcal{H}$ to $\mathbb{R}^3$.

$\boldsymbol{\xi} = \mathbf{x}' - \mathbf{x}$ is a bond. $\underline{\mathbf{A}}\langle\boldsymbol{\xi}\rangle$ is a vector.

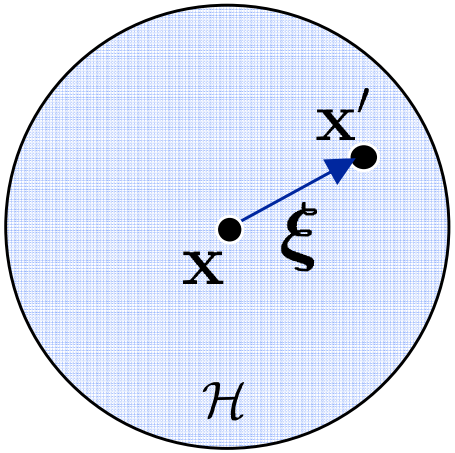

$\mathcal{H}$= set of all bonds connected to $\mathbf{x}$

A vector state is like a 2nd order tensor, except:

- A vector state can be nonlinear.
- A vector state can be discontinuous.

Sandia National Laboratories

Deformation states

The deformation state $\underline{\mathbf{Y}}[\mathbf{x}, t]$ maps any bond connected to $\mathbf{x}$ into its deformed image.

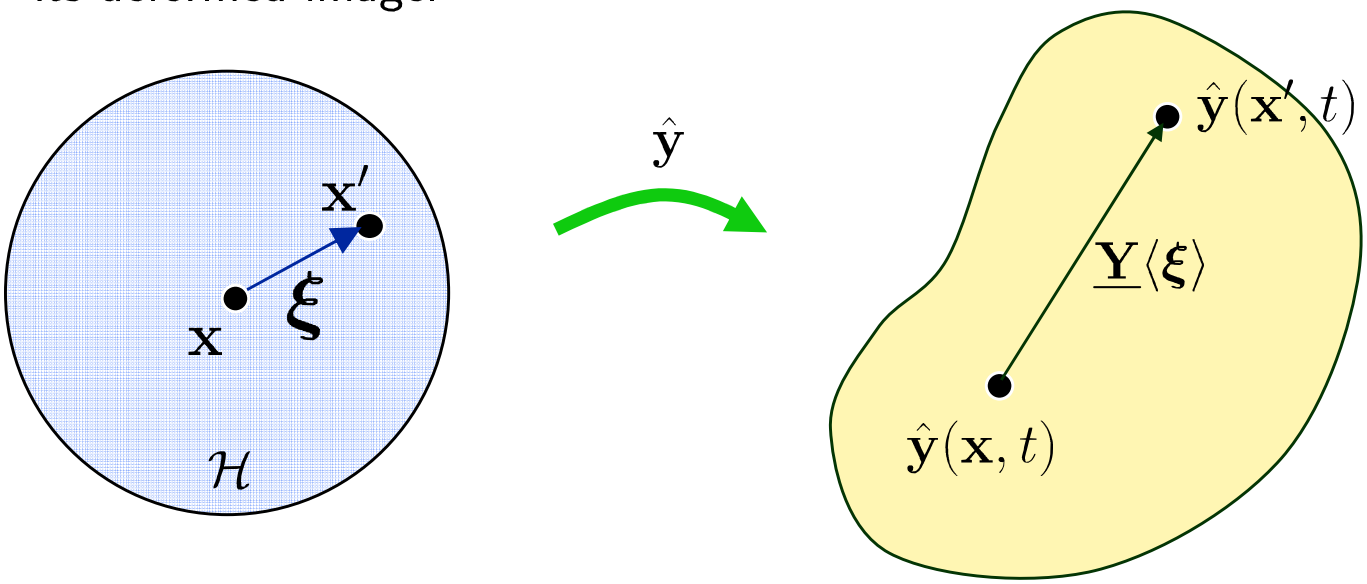

$$\underline{\mathbf{Y}}[\mathbf{x}, t]\langle\mathbf{x}' - \mathbf{x}\rangle = \hat{\mathbf{y}}(\mathbf{x}', t) - \hat{\mathbf{y}}(\mathbf{x}, t)$$

Sandia National Laboratories

Deformation states contain a lot of kinematical complexity

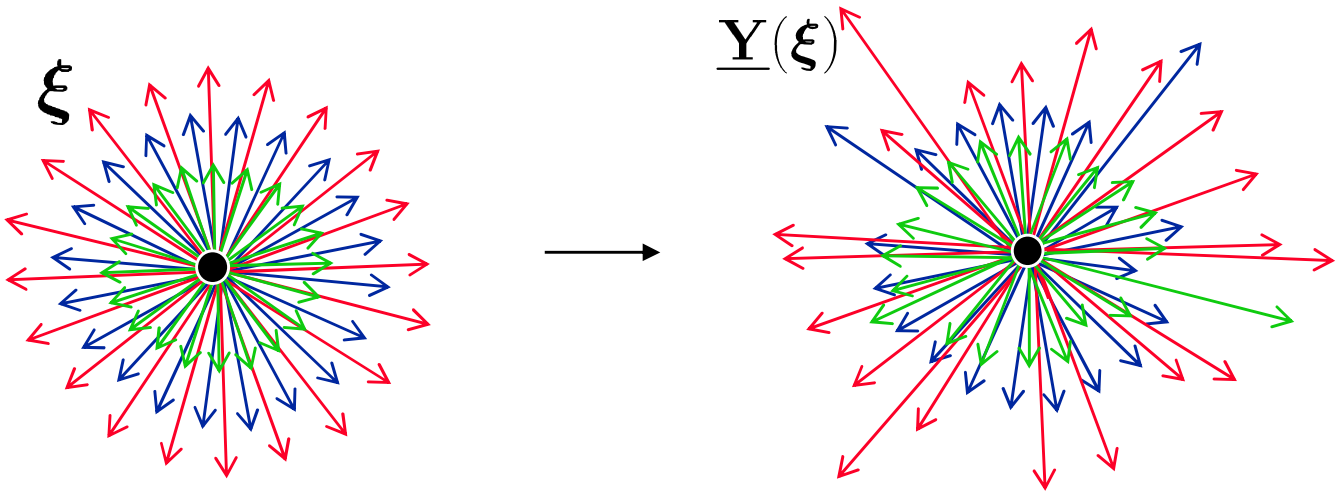

Undeformed bonds connected to $\mathbf{x}$ Deformed bonds connected to $\mathbf{x}$

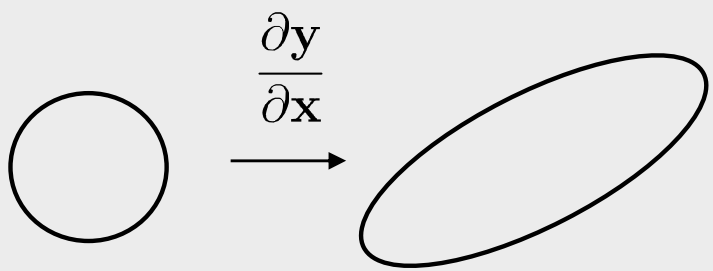

Compare this with standard theory in which small spheres are mapped into ellipsoids

Sandia National Laboratories

Elastic materials

Strain energy density at $\mathbf{x}$ depends only on the deformation state there:

$$W(\mathbf{x}, t) = \hat{W}(\underline{\mathbf{Y}}[\mathbf{x}, t])$$

Is this really so different from the standard theory?

Standard:

$$\hat{W}\left(\frac{\partial \hat{\mathbf{y}}}{\partial \mathbf{x}}\right)$$

Energy depends on a linear transformation

Peridynamic:

$$\hat{W}(\underline{\mathbf{Y}})$$

Energy depends on a nonlinear transformation

Sandia National Laboratories

Potential energy statement leads to the peridynamic equation of equilibrium

Define the potential energy in a body $\mathcal{B}$ by

$$\Phi_{\mathbf{u}} = \int_{\mathcal{B}} W \, dV - \int_{\mathcal{B}} \mathbf{u} \cdot \mathbf{b} \, dV.$$

$\delta\Phi_{\mathbf{u}} = 0$ yields the Euler-Lagrange equation

$$\int_{\mathcal{H}} \left(\underline{\mathbf{T}}[\mathbf{x}]\langle \mathbf{x}' - \mathbf{x} \rangle - \underline{\mathbf{T}}[\mathbf{x}']\langle \mathbf{x} - \mathbf{x}' \rangle \right) dV_{\mathbf{x}'} + \mathbf{b}(\mathbf{x}) = \mathbf{0}$$

for all $\mathbf{x} \in \mathcal{B}$, where $\underline{\mathbf{T}}[\mathbf{x}]$ is the *force state* at $\mathbf{x}$ defined by

$$\underline{\mathbf{T}} = \nabla W(\underline{\mathbf{Y}})$$

where ∇ indicates the Frechet derivative.

Sandia National Laboratories

Meaning of the Frechet derivative

The force density $\underline{\mathbf{T}}\langle\xi\rangle$ in bond ξ is found by varying the bond displacement and evaluating the change in W.

$$\delta W(\xi) = \underline{\mathbf{T}}\langle\xi\rangle \cdot \delta\underline{\mathbf{Y}}\langle\xi\rangle$$

Thus the *force state* $\underline{\mathbf{T}}$ is the the work conjugate of $\underline{\mathbf{Y}}$:

$$\delta W = \int_{\mathcal{H}} \underline{\mathbf{T}}\langle\xi\rangle \cdot \delta\underline{\mathbf{Y}}\langle\xi\rangle \, dV_\xi$$

Compare with standard theory: $\delta W = \sigma \cdot \delta\mathbf{F}$

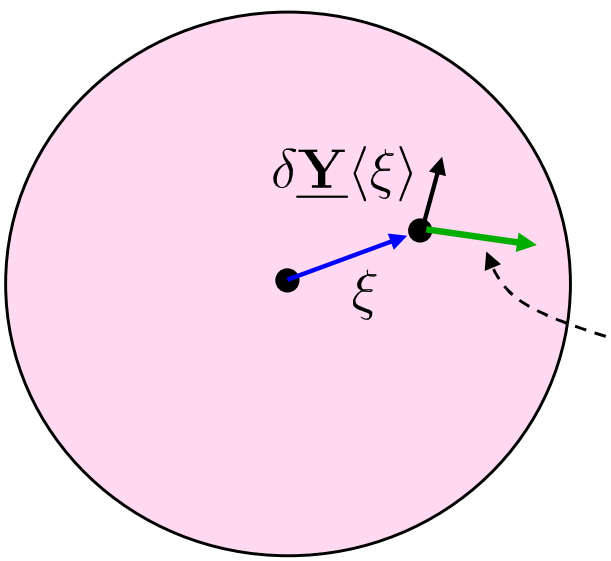

$\underline{\mathbf{T}}\langle\xi\rangle$=bond force density (dimensions force/volume^2)

Sandia National Laboratories

Force states and bond force

The total force density in bond $\mathbf{x}' - \mathbf{x}$ is composed of 2 parts:

$$\mathbf{f}(\mathbf{x}', \mathbf{x}, t) = \underline{\mathbf{T}}[\mathbf{x}]\langle \mathbf{x}' - \mathbf{x} \rangle - \underline{\mathbf{T}}[\mathbf{x}']\langle \mathbf{x} - \mathbf{x}' \rangle.$$

The equation of motion is

$$\rho(\mathbf{x})\ddot{\mathbf{u}}(\mathbf{x}, t) = \int_{\mathcal{H}} \mathbf{f}(\mathbf{x}', \mathbf{x}, t)\, dV_{\mathbf{x}'} + \mathbf{b}(\mathbf{x}, t)$$

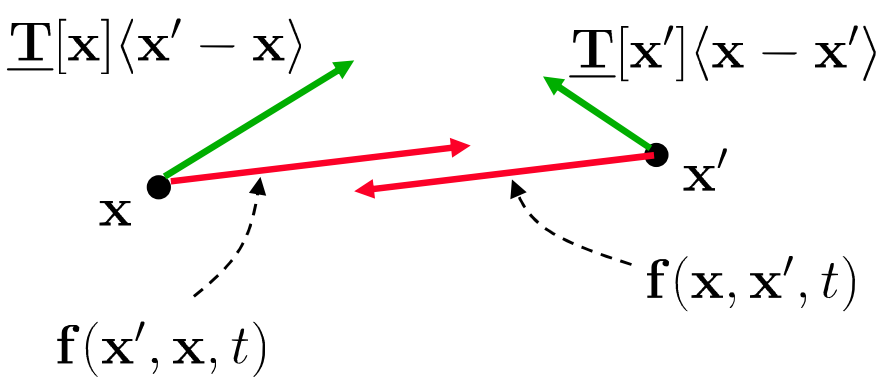

Sandia National Laboratories

Peridynamic stress tensor

The peridynamic stress tensor is defined by

$$\boldsymbol{\nu}(\mathbf{x}) = \int_{\mathcal{S}} \int_0^\infty \int_0^\infty (y+z)^2 \mathbf{f}(\mathbf{x}+y\mathbf{m}, \mathbf{x}-z\mathbf{m}) \otimes \mathbf{m} \, dz \, dy \, d\Omega_{\mathbf{m}}$$

where $\mathcal{S}$ is the unit sphere and $d\Omega_{\mathbf{m}}$ is a differential solid angle in the direction of a unit vector $\mathbf{m}$.

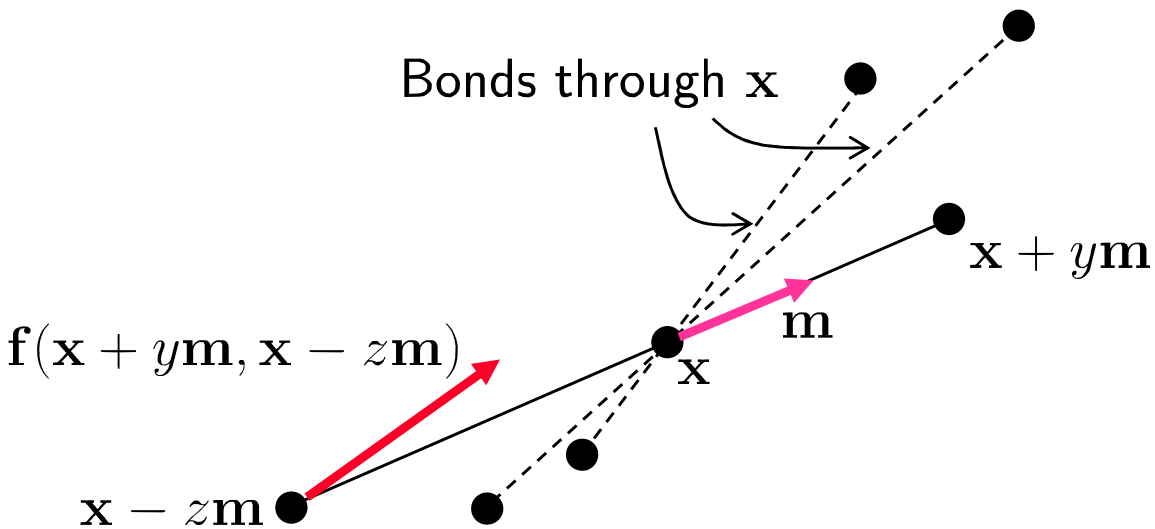

Sandia National Laboratories

Properties of the peridynamic stress tensor

- The force per unit area at $\mathbf{x}$ through a plane with normal $\mathbf{n}$ is

$$\mathbf{s} = \boldsymbol{\nu}(\mathbf{x})\mathbf{n}$$

- The peridynamic equation of motion can be written as

$$\rho\ddot{\mathbf{u}} = \nabla \cdot \boldsymbol{\nu} + \mathbf{b}$$

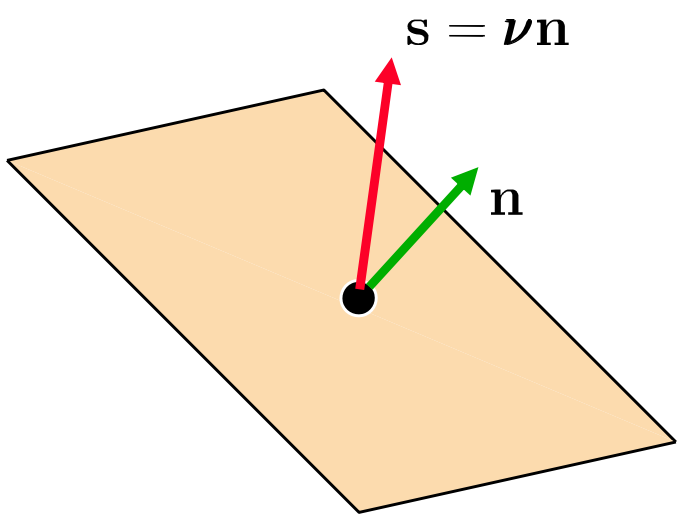

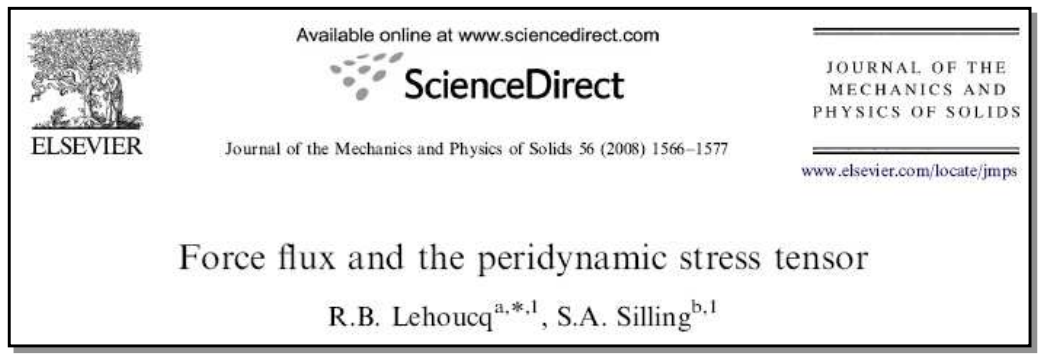
Available online at www.sciencedirect.com

ScienceDirect

ELSEVIER

Journal of the Mechanics and Physics of Solids 56 (2008) 1566–1577

JOURNAL OF THE MECHANICS AND PHYSICS OF SOLIDS

www.elsevier.com/locate/jmps

Force flux and the peridynamic stress tensor

R.B. Lehoucq[a,*,1], S.A. Silling[b,1]

Sandia National Laboratories

Convergence of peridynamics to the standard theory

- If the only requirement on a material model is that it reproduce bulk response under homogeneous deformation, then the horizon (length scale) is arbitrary.
- If we shrink the horizon to zero, the PD equations converge to the classical PDEs.
  - This result holds only if the deformation is smooth.

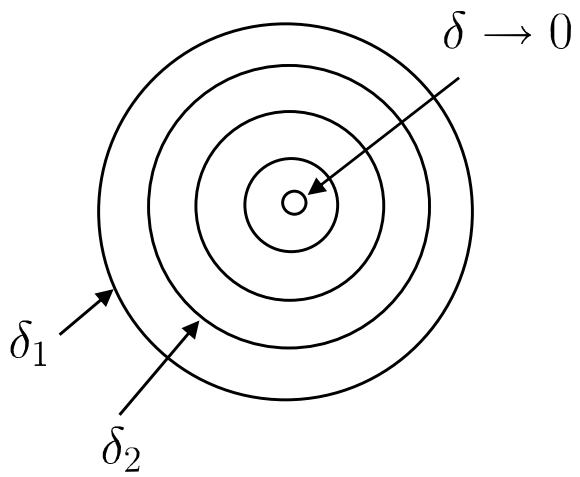

As $\delta \to 0$,

$$\nu(\underline{\mathbf{Y}}) \to \sigma(\mathbf{F}), \qquad \mathbf{F} = \frac{\partial \hat{\mathbf{y}}}{\partial \mathbf{x}}$$

hence

$$\int_{\mathcal{H}} \mathbf{f}\, dV \to \nabla \cdot \sigma$$

Sandia National Laboratories

Bond-based peridynamic model

An important special case is when bonds respond independently of each other:

$$\rho\ddot{\mathbf{u}}(\mathbf{x},t) = \int_{\mathcal{H}} \mathbf{f}(\mathbf{u}(\mathbf{x}',t) - \mathbf{u}(\mathbf{x},t), \mathbf{x}' - \mathbf{x})\, dV_{\mathbf{x}'} + \mathbf{b}(\mathbf{x},t),$$

Unlike the general case, here each $\mathbf{f}$ depends only on the deformation of that particular bond.

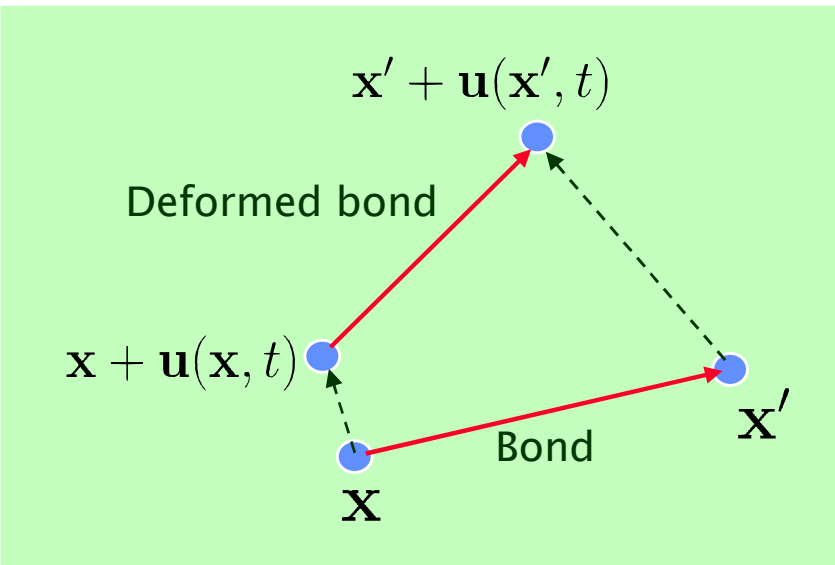

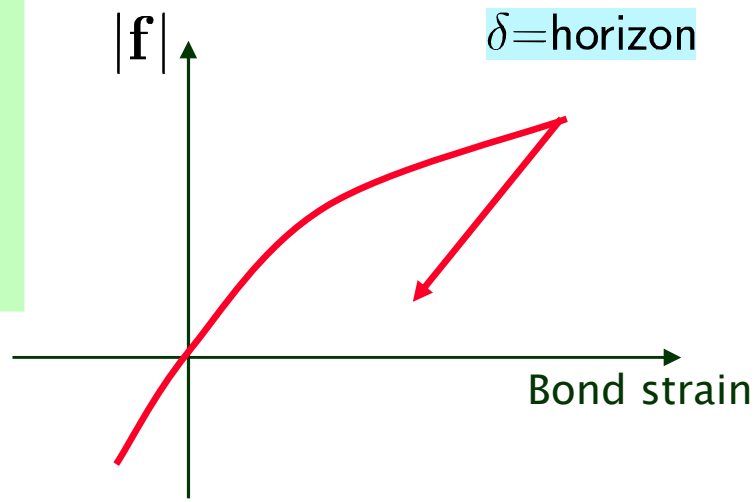

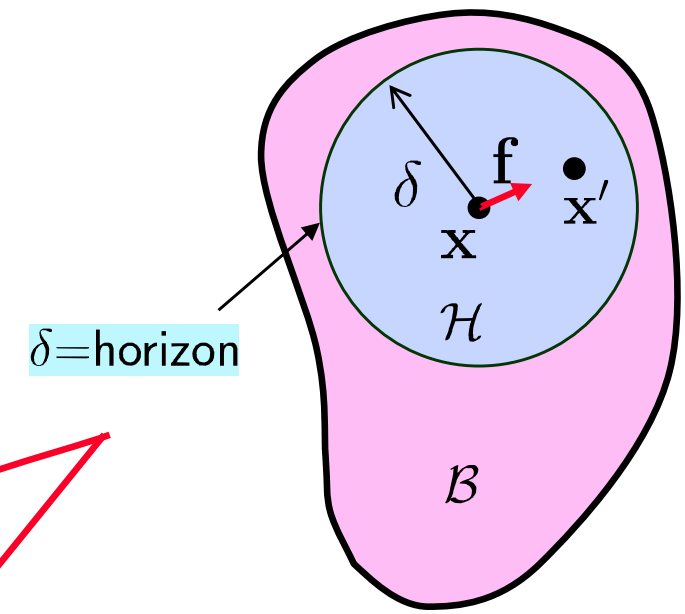

Sandia National Laboratories

Damage is introduced through irreversible bond breakage

Two examples of material models that include damage:

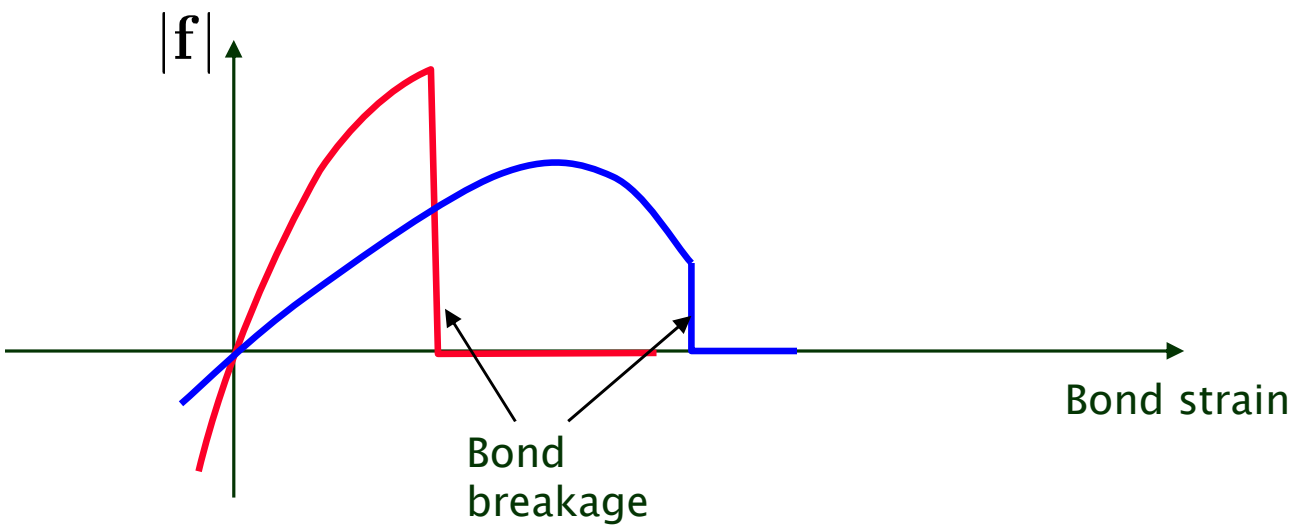

Sandia National Laboratories

How fracture occurs in a peridynamic body

- As it stretches:
  - First it deforms continuously.
  - Then a material instability occurs, nucleating a crack.
  - Then the crack advances autonomously.

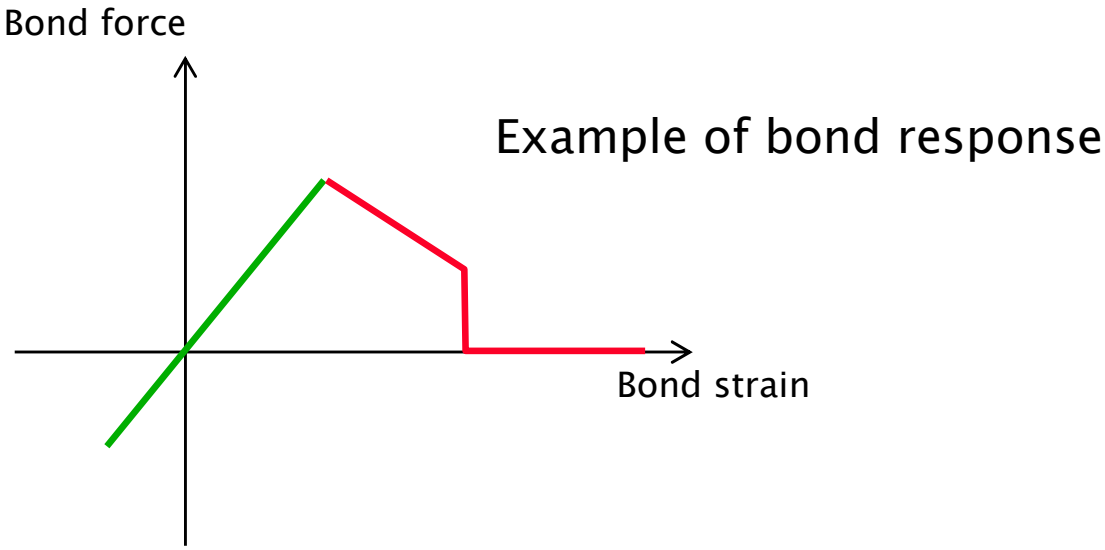

Sandia National Laboratories

Material instability and damage

- Assume a homogeneous deformation of this peridynamic material.
- When enough bonds stretch past the peak, material instability occurs.

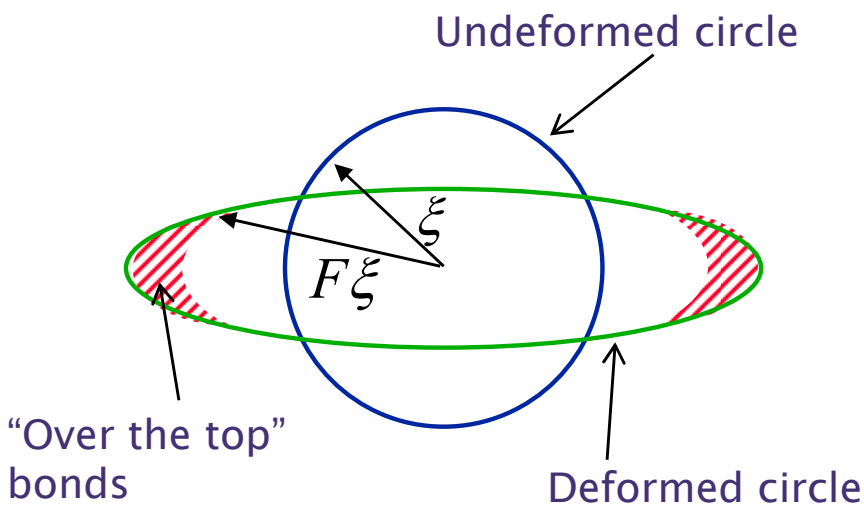

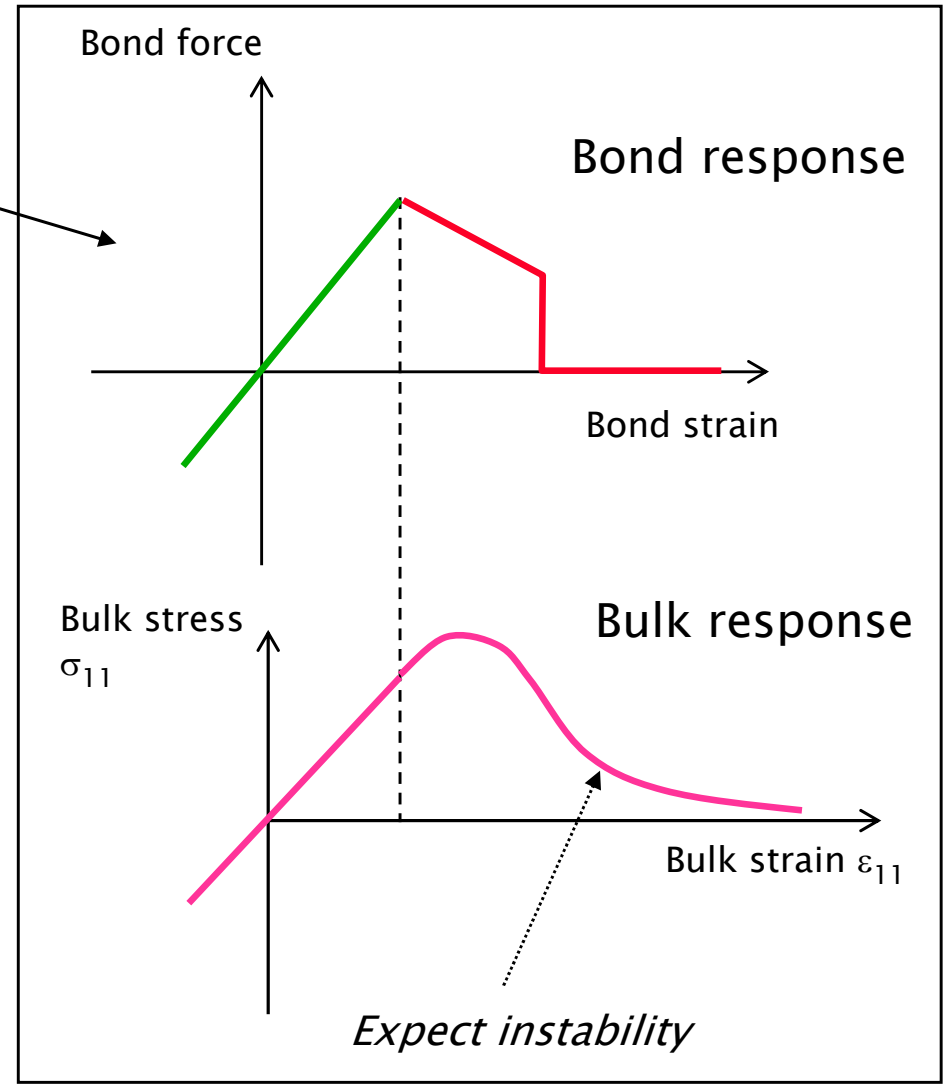

Crack nucleation condition

- What material stability governs the spontaneous growth of a discontinuity in $\mathbf{u}$?
- Define a symmetric tensor field by

$$\mathbf{P}(\mathbf{x}) = \int\int \nabla\nabla W\langle \boldsymbol{\xi}, \boldsymbol{\zeta}\rangle \, dV_{\boldsymbol{\zeta}} \, dV_{\boldsymbol{\xi}}$$

2nd Frechet derivative

- Can show

$$\rho[\ddot{\mathbf{u}}] = -\mathbf{P}[\mathbf{u}]$$

therefore $[\ddot{\mathbf{u}}] \cdot [\mathbf{u}] \geq 0$ if and only if $\mathbf{P}$ is *not* positive definite.

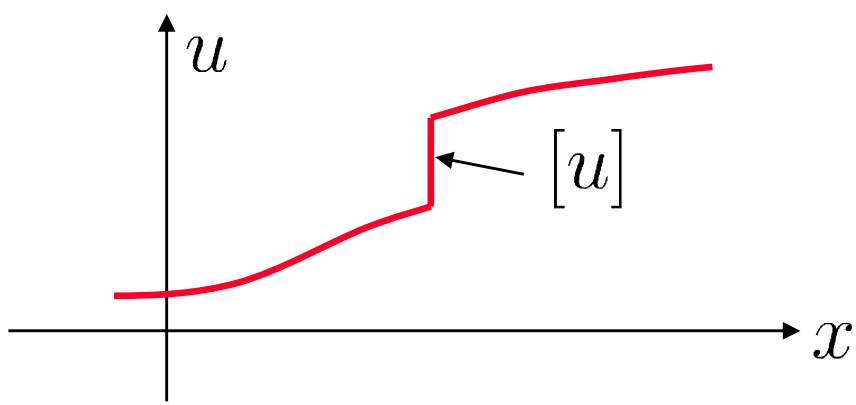

Sandia National Laboratories

Energy required to advance a crack

- Adding up the work needed to break all bonds across a plane yields the energy release rate:

$$G = \int_0^\delta \int_{R_+} w_0(\boldsymbol{\xi})\, dV_{\boldsymbol{\xi}}\, ds$$

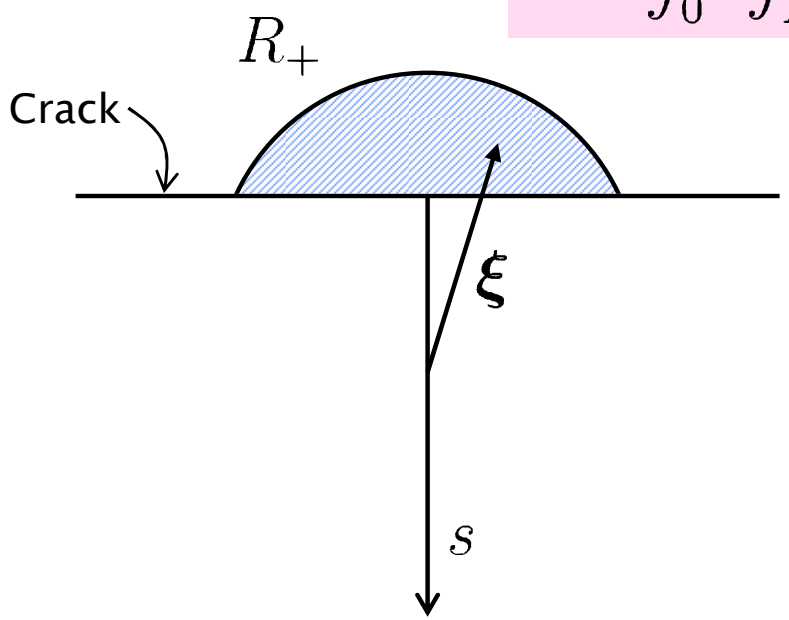

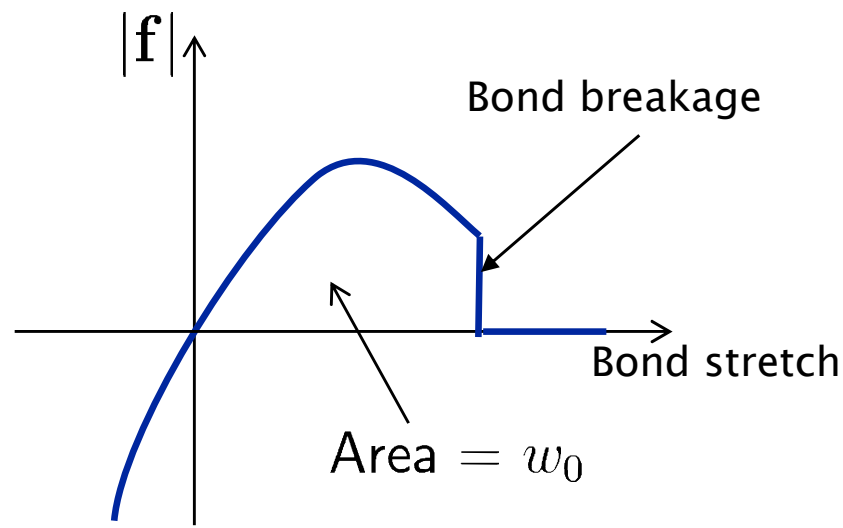

$w_0 =$ work (per unit volume^2) required to break one bond

There is also a version of the J-integral that applies in this theory.

Sandia National Laboratories

Some nonlocal models and their relation to PD

- Navier (1820's, pre-Cauchy):
  - Solid as a collection of separated particles but linearized kinematics.
    - PD: nonlinear kinematics, not restricted to central potentials.
- Kroner, Edelen, Eringen, Kunin, Krumhansl, others (1960's on):
  - Continuum treatment of a lattice by averaging of strains over a volume.
  - Quasicontinuum formulated in terms of displacement.
    - PD: similar but nonlinear, allows damage, discontinuities.
- Bazant, Belytschko, others (1980's on):
  - Nonlocality in damage while retaining classical PDEs.
    - PD: damage included through constitutive treatment of bonds.
- Barenblatt, Dugdale, Hillerborg, Bazant, others (1960's on):
  - Cohesive crack models.
    - PD: cohesion across crack faces results from process of bond damage.
- Coleman, Aifantis, Hutchinson, Fleck, others (1950's on):
  - Gradient theories of elasticity and plasiticity ("weak nonlocality").
    - PD: strongly nonlocal, explicitly allows discontinuities.
- Lattice models, discrete elements, Cusatis model (1960's on):
    - PD is a continuum theory, but when discretized is similar to a lattice model.

Sandia National Laboratories

Outline

- Objective
- Theory
- EMU numerical method
- Examples
- Heterogeneity and nonlocality
- Fragmentation

Sandia National Laboratories

EMU numerical method

- Integral is replaced by a finite sum: resulting method is meshless and Lagrangian.

$$\rho\ddot{\mathbf{u}}(\mathbf{x},t) = \int_{\mathcal{H}} \mathbf{f}(\mathbf{u}(\mathbf{x}',t) - \mathbf{u}(\mathbf{x},t), \mathbf{x}' - \mathbf{x})\, dV_{\mathbf{x}'} + \mathbf{b}(\mathbf{x},t)$$

$$\downarrow$$

$$\rho\ddot{\mathbf{u}}_i^n = \sum_{k\in\mathcal{H}} \mathbf{f}(\mathbf{u}_k^n - \mathbf{u}_i^n, \mathbf{x}_k - \mathbf{x}_i)\, \Delta V_k + \mathbf{b}_i^n$$

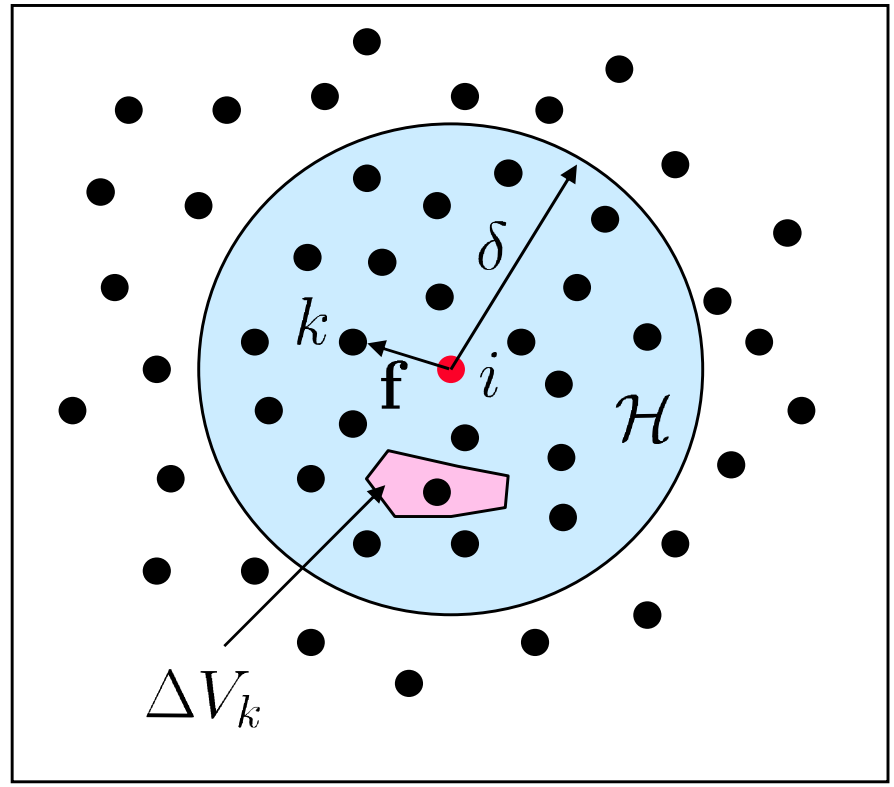

Sandia National Laboratories

Outline

- Objective
- Theory
- EMU numerical method
- Examples
- Heterogeneity and nonlocality
- Fragmentation

Sandia National Laboratories

Crack nucleation

- A maximum in the bond force curve leads to crack nucleation at a prescribed strain independent of the breakage stretch.

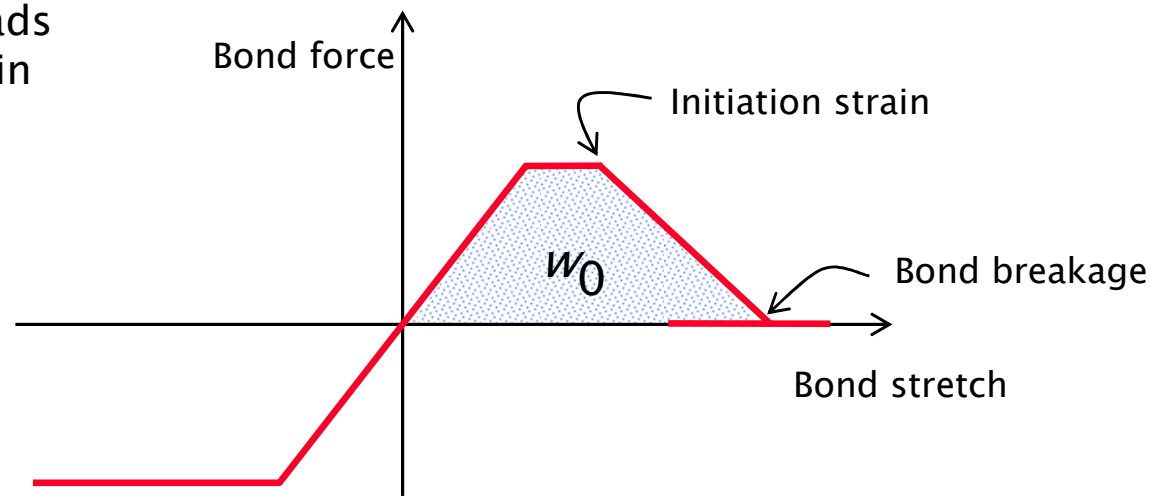

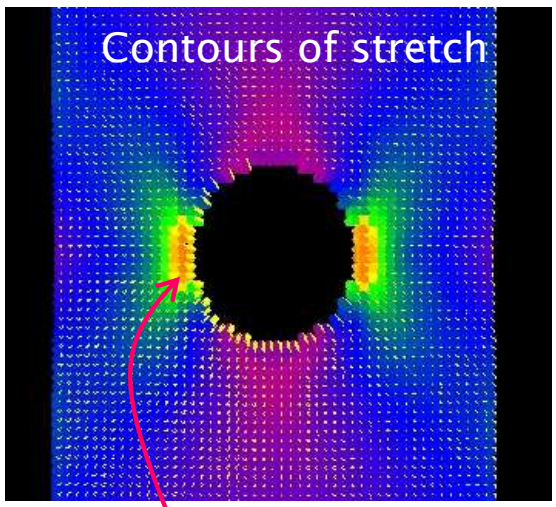

Stretch > initiation strain leads to crack initiation

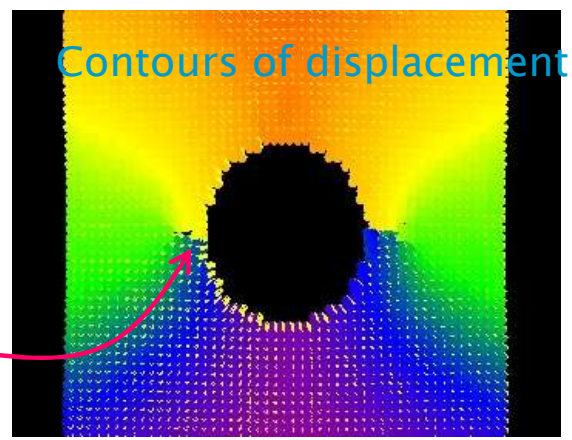

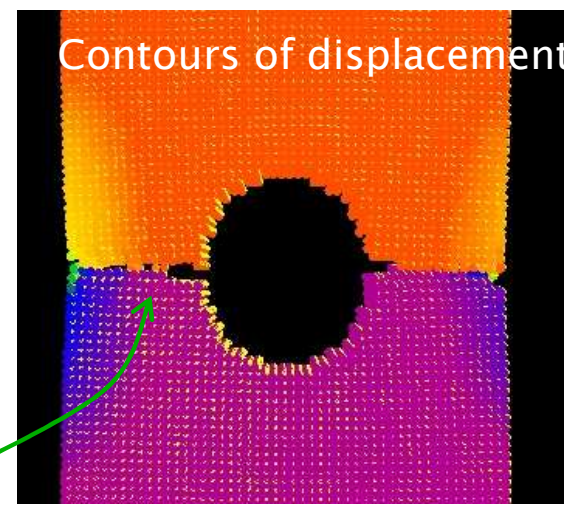

Crack initiation leads to dynamic fracture

Sandia National Laboratories

Predicted crack growth direction depends continuously on loading direction

- Plate with a pre-existing defect is subjected to prescribed boundary velocities.
- These BC correspond to mostly Mode-I loading with a little Mode-II.

$$\dot{\varepsilon} = (0.25\mathrm{s}^{-1}) \begin{bmatrix} 0 & 0.1 \\ 0 & 1 \end{bmatrix}$$

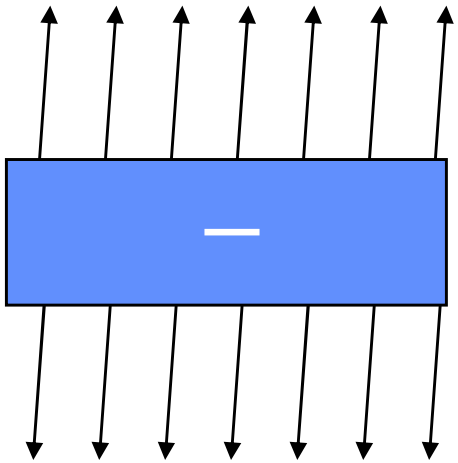

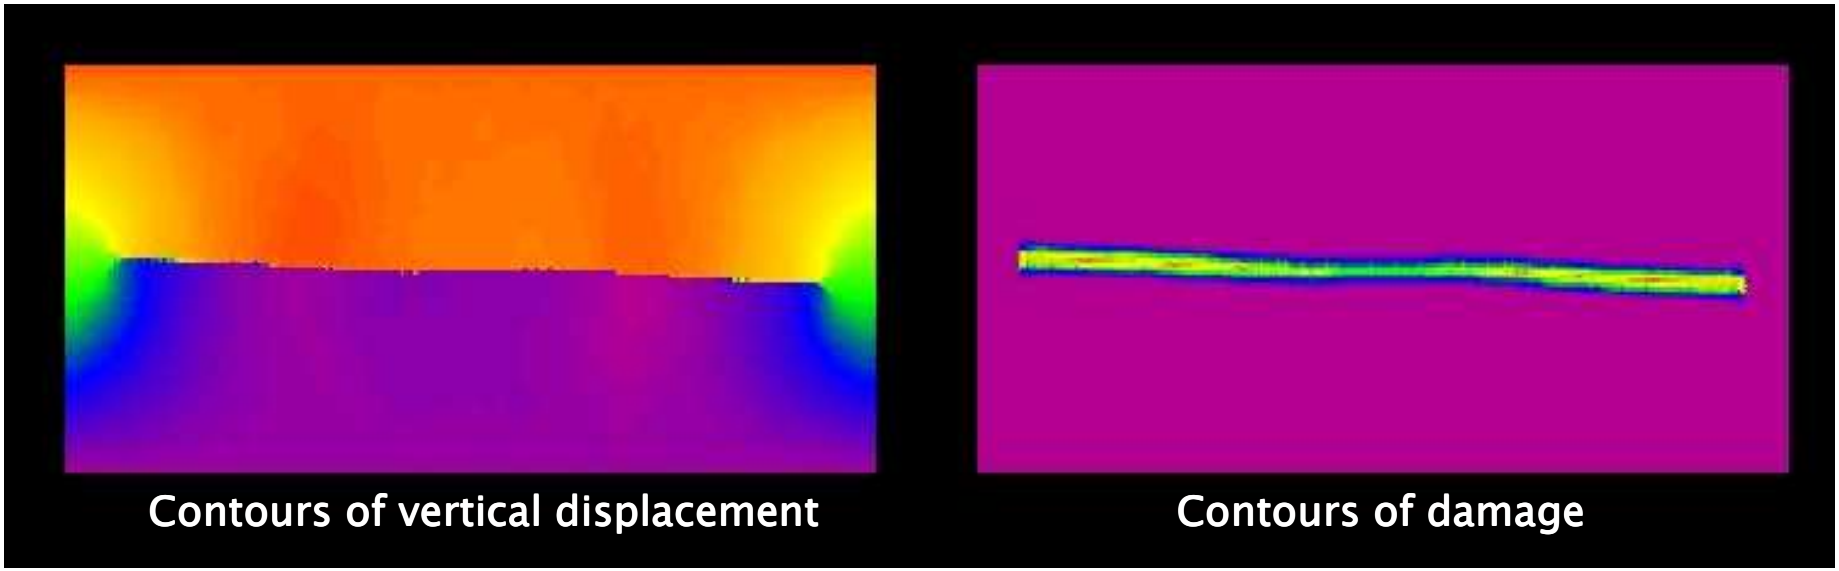

Contours of vertical displacement

Contours of damage

Sandia National Laboratories

Effect of rotating the grid in the "mostly Mode-I" problem



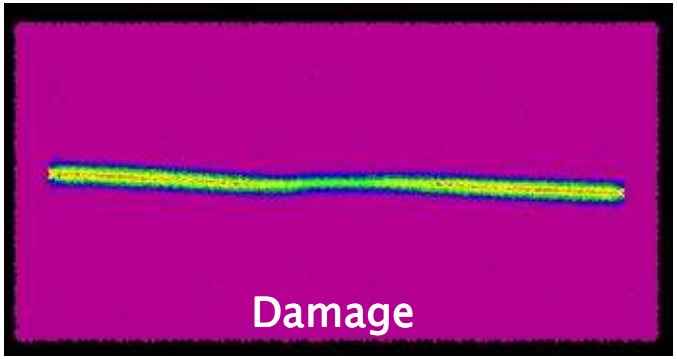

Original grid direction



Rotated grid direction

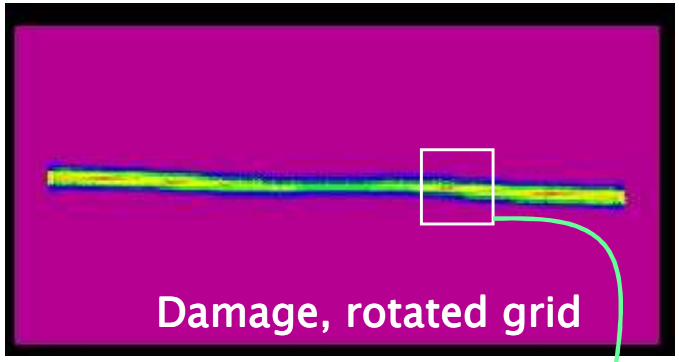

Network of identical bonds in many directions allows cracks to grow in any direction.

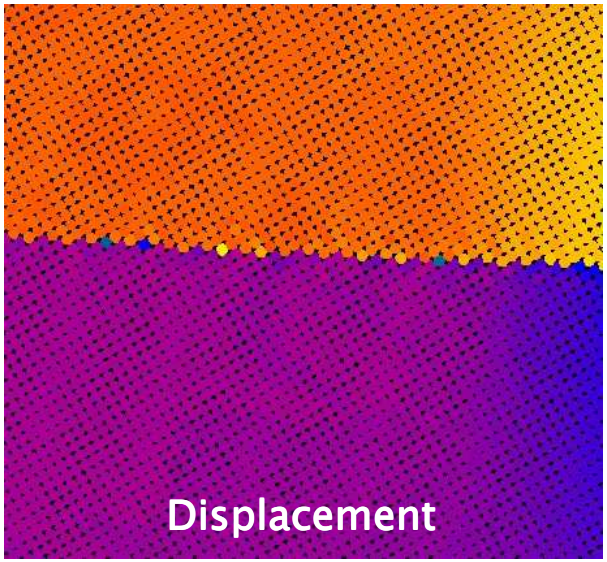

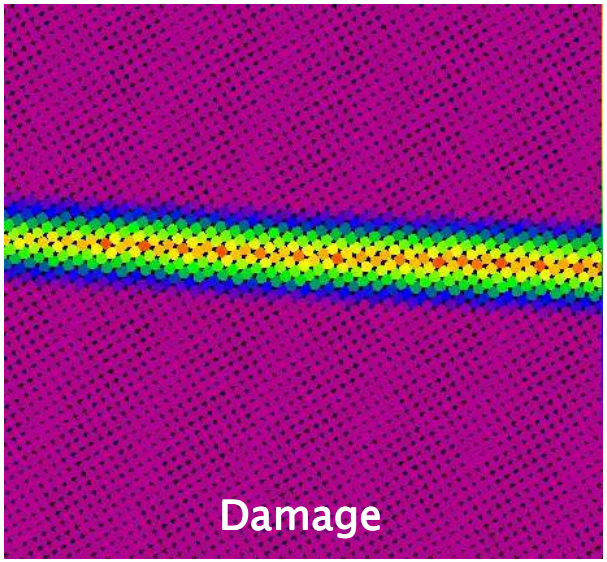

Sandia National Laboratories

Crack tip fields in the “mostly Mode-I” problem



Rotated grid direction

Nodal displacements shown below are x200.

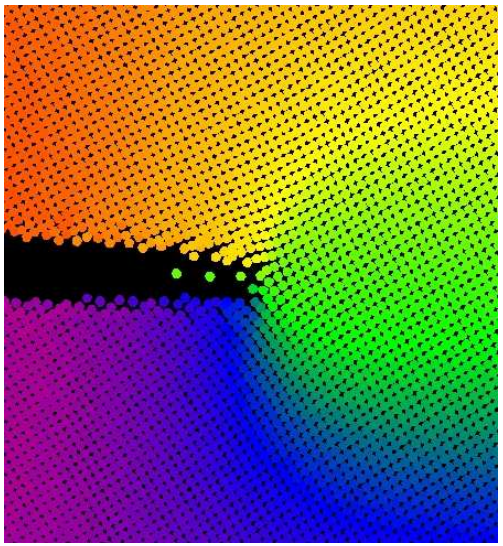

Contours of vertical displacement

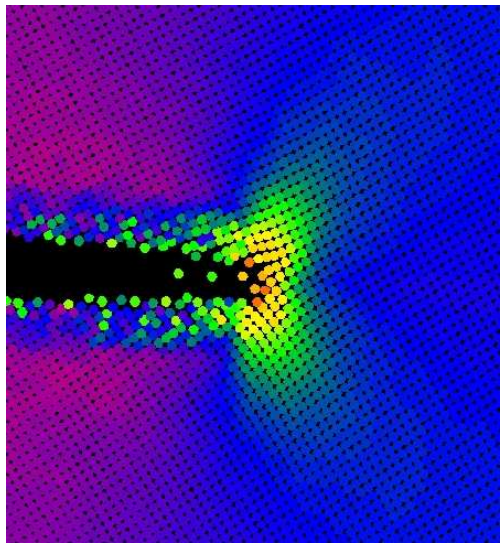

Contours of maximum bond stretch (similar to max principal strain)

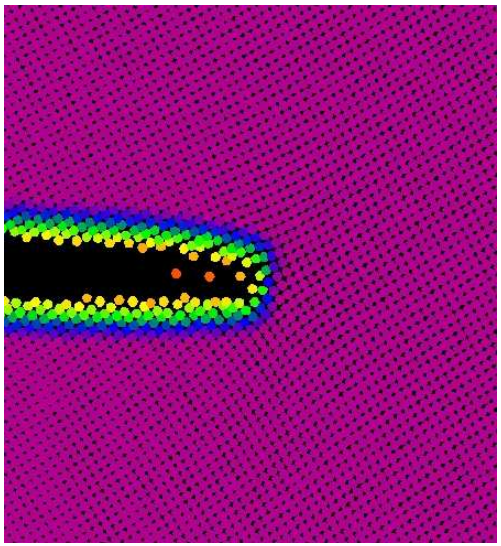

Contours of damage

Sandia National Laboratories

Peridynamic model of a 6061-aluminum bar

- EMU simulation with large-deformation, strain-hardening, rate-dependent material model.
  - Material model implementation by J. Foster, SNL 5431.

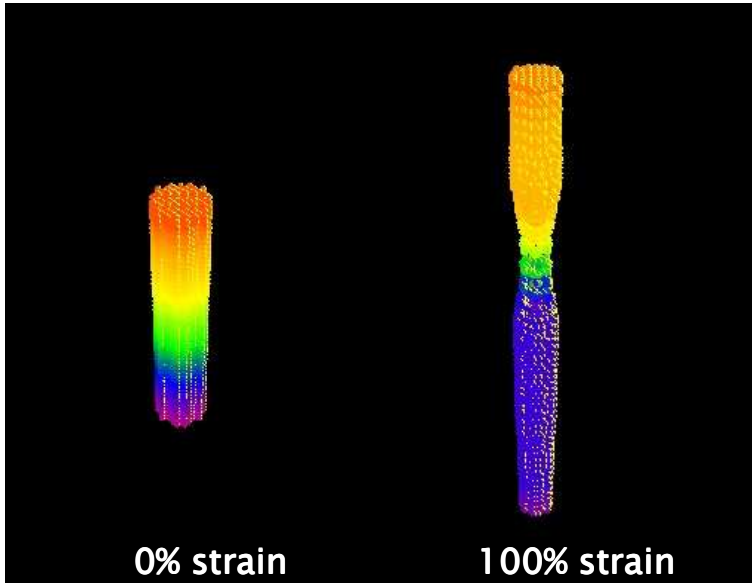

Necking under tension

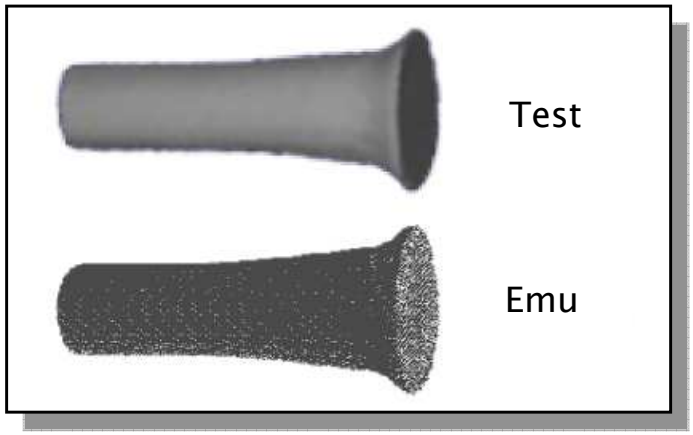

Taylor impact test
(J. Foster)

Sandia National Laboratories

Crack branching*

Peridynamic simulations of dynamic crack growth with 4 grid spacings (horizon = 3Δx)

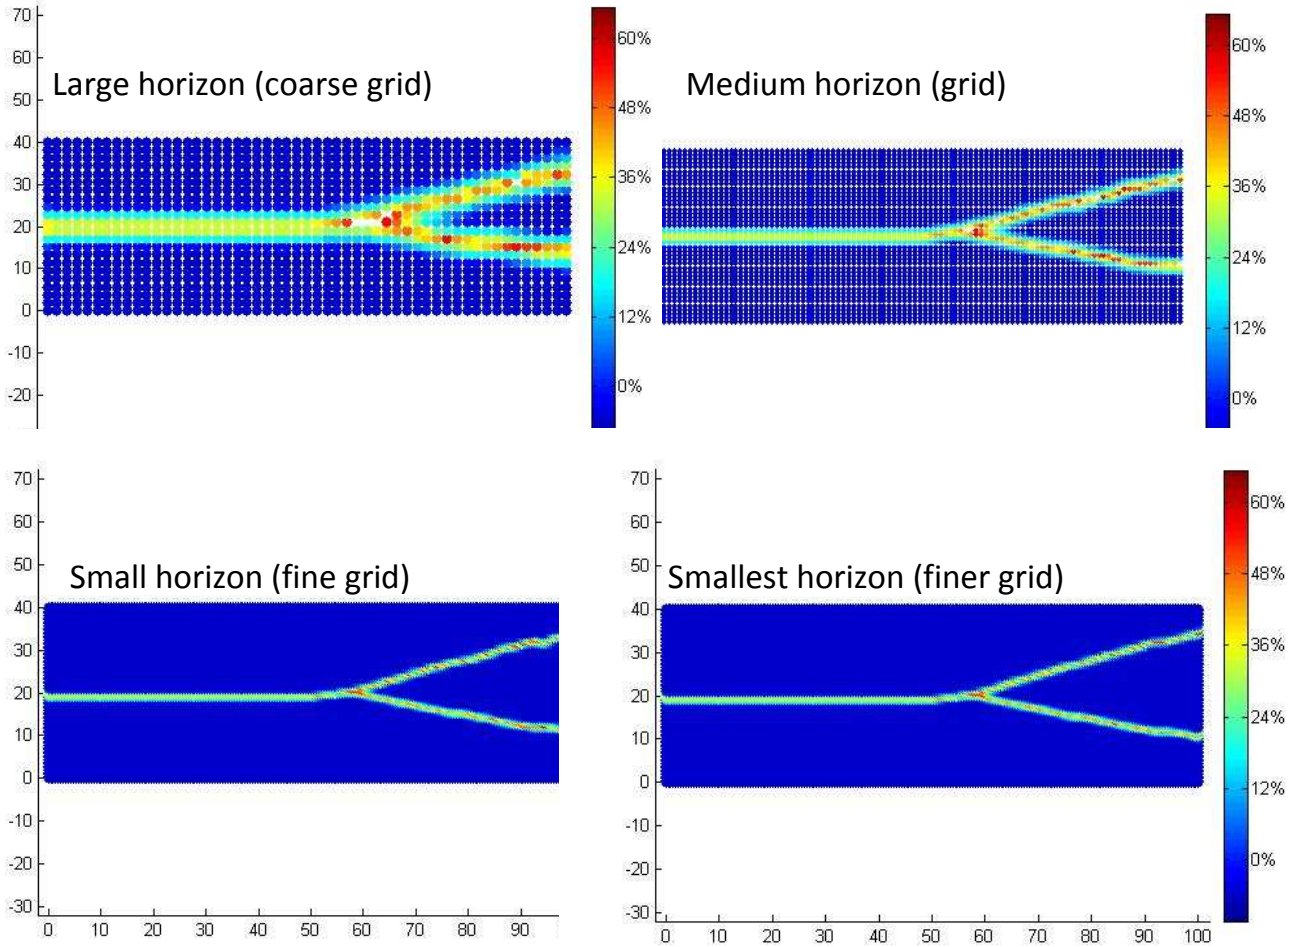

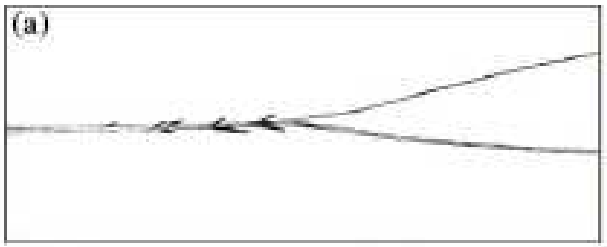

Crack branching experimental results for a single edge notch specimen of homalite-100 (Ramulu and Kobayashi, IJFM 1985).

* Work by F. Bobaru & students

Sandia National Laboratories

Bond based PD: Damage in composites (Boeing)

- How does the fraction of fibers in each direction affect the direction of crack growth?
- What damage occurs when a composite panel is struck by hail?

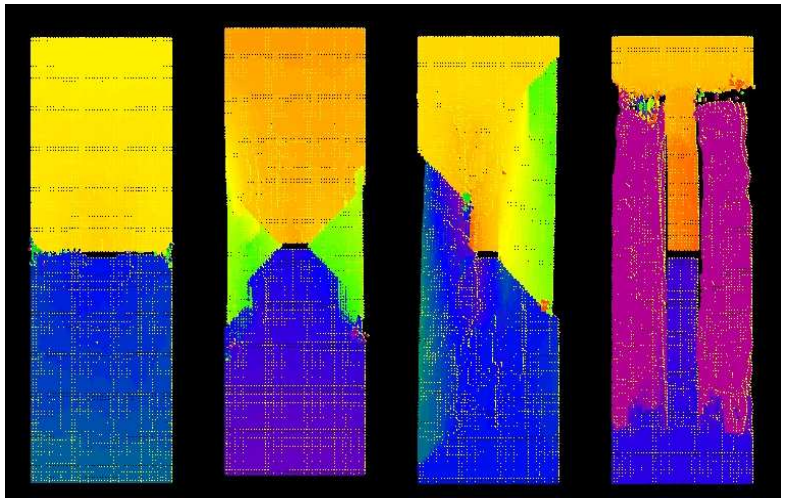

Crack growth in a notched panel

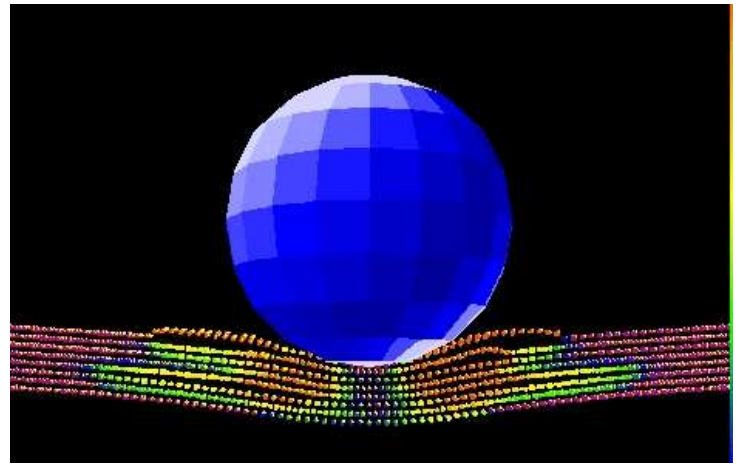

Delamination caused by impact

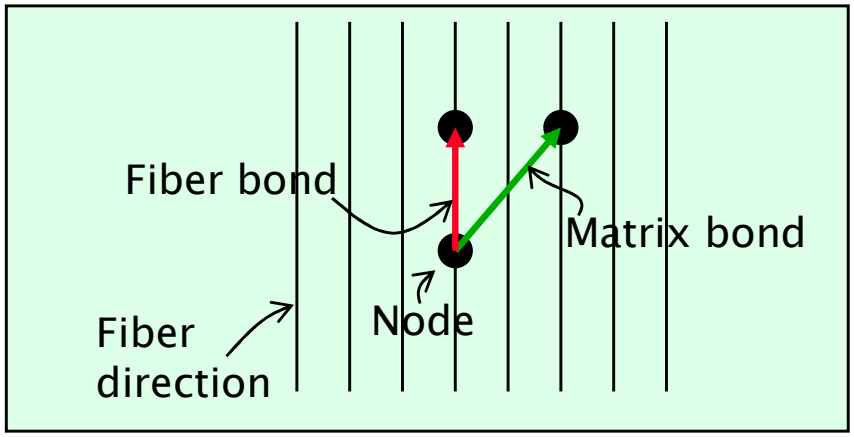

Sandia National Laboratories

Polycrystals: Mesoscale model*

- What is the effect of grain boundaries on the fracture of a polycrystal?

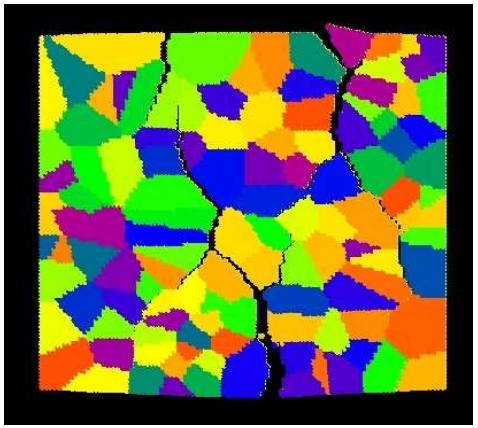

β = 0.25

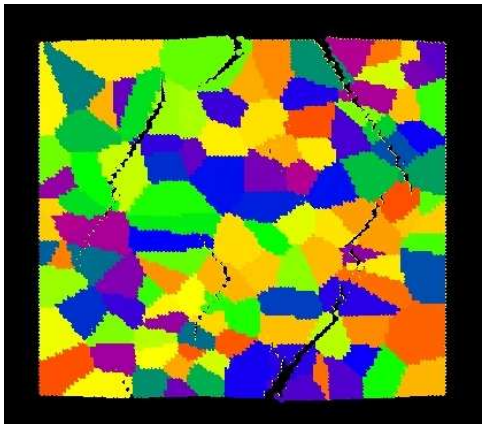

β = 1

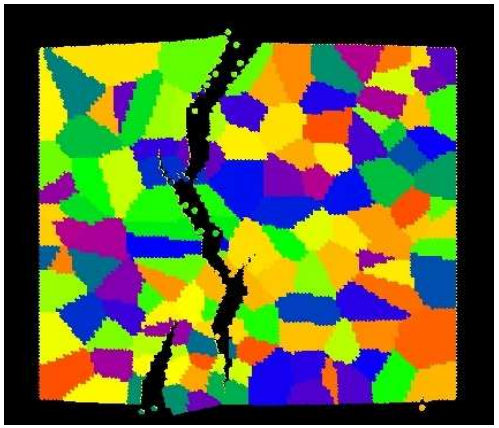

β = 4

$$\beta = \frac{s_i^*}{s_g^*}$$

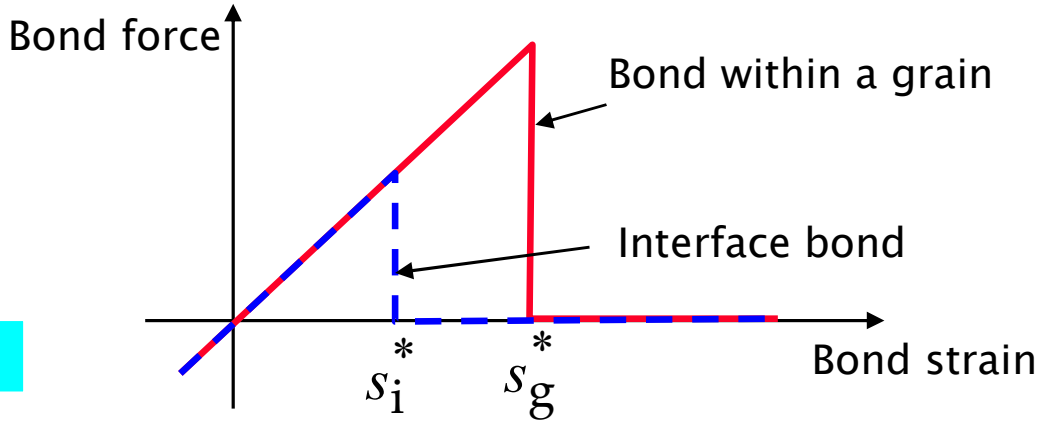

Large β favors intra(trans)-granular fracture.

* Work by F. Bobaru & students

Sandia National Laboratories

Outline

- Objective
- Theory
- EMU numerical method
- Examples
- Heterogeneity and nonlocality
- Fragmentation

Sandia National Laboratories

Nonlocality and length scales

- Many physical problems have some natural length scale.
  - Sometimes the length scale is obvious, e.g.,
    - Interatomic forces
    - Molecular dynamics cannot be done without nonlocality.

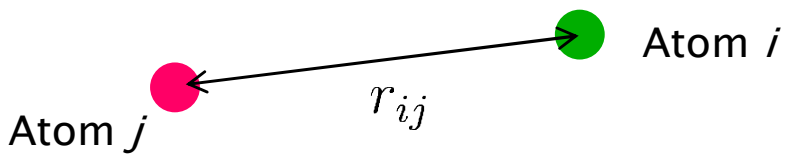

$$F_{ij} \sim \left(\frac{a}{r_{ij}}\right)^{12} - \left(\frac{a}{r_{ij}}\right)^{6}$$

Nonlocality and length scales: surface forces

- Sometimes the length scale is a little less obvious, e.g.
  - van der Waals forces that lead to longer-range surface forces.
  - Force between a pair of atoms as they are separated:

$$F_{ij} \sim 1/r_{ij}^6$$

  - Net force between halfspace and a sphere made of many of these atoms* occurs over a much larger length scale:

$$F_{\text{sphere}} \sim 1/D$$

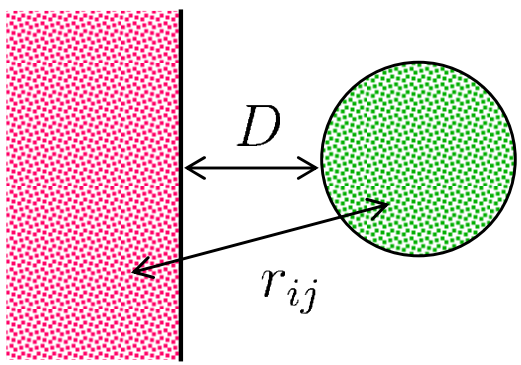

See J. Israelachvili, *Intermolecular and Surfaces Forces*, pp. 177.

Sandia National Laboratories

Nonlocality and length scales: composites

- In a composite, the applicable length scale could be much greater than the fiber diameter or ply thickness.

$$P >> D_{\text{fiber}}$$

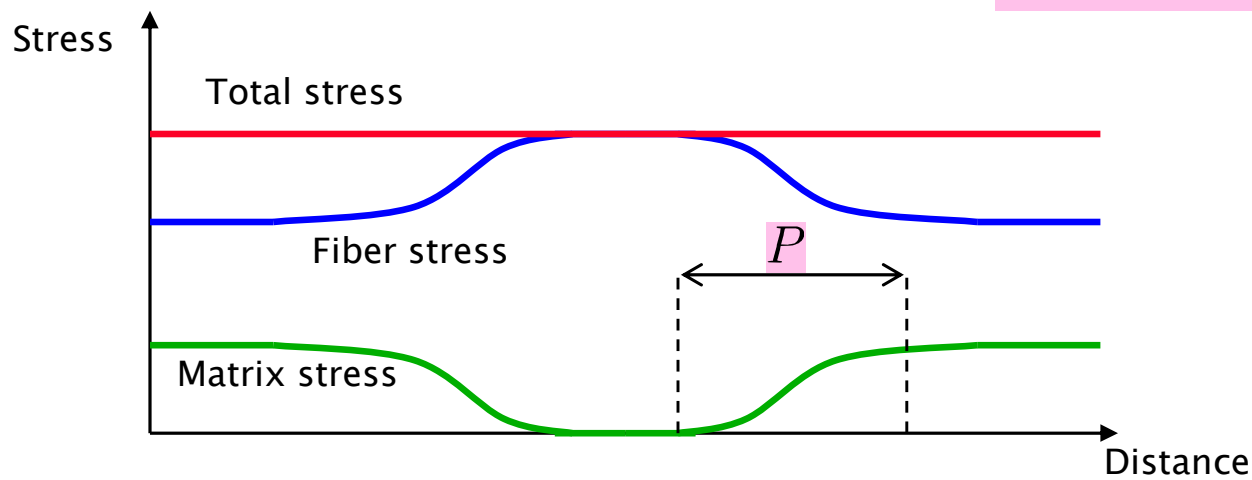

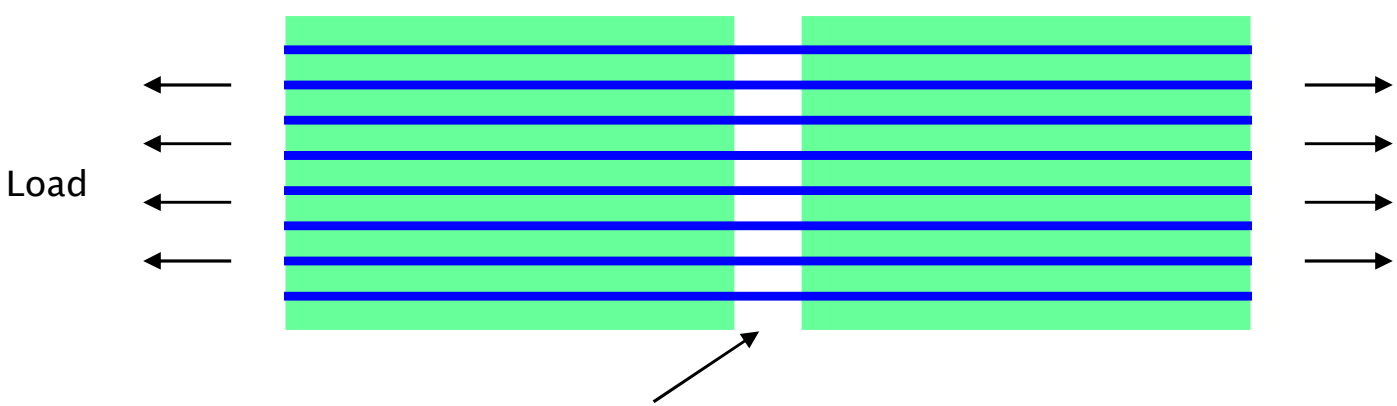

Fiber-reinforced composite with a gap in the matrix ("bridging")

Sandia National Laboratories

Nonlocality as a result of homogenization

- Homogenization, neglecting the natural length scales of a system, often doesn't give good answers.

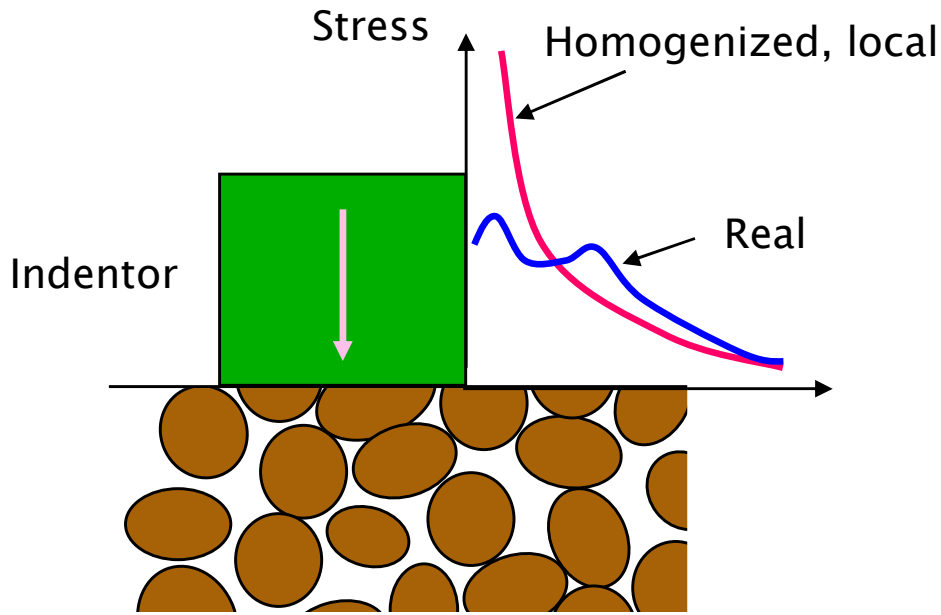

Claim: Nonlocality is an essential feature of a realistic homogenized model of a heterogeneous material.

Proposed experimental method for measuring the peridynamic horizon

- Measure how much a step wave spreads as it goes through a sample.
- Fit the horizon in a 1D peridynamic model to match the observed spread.

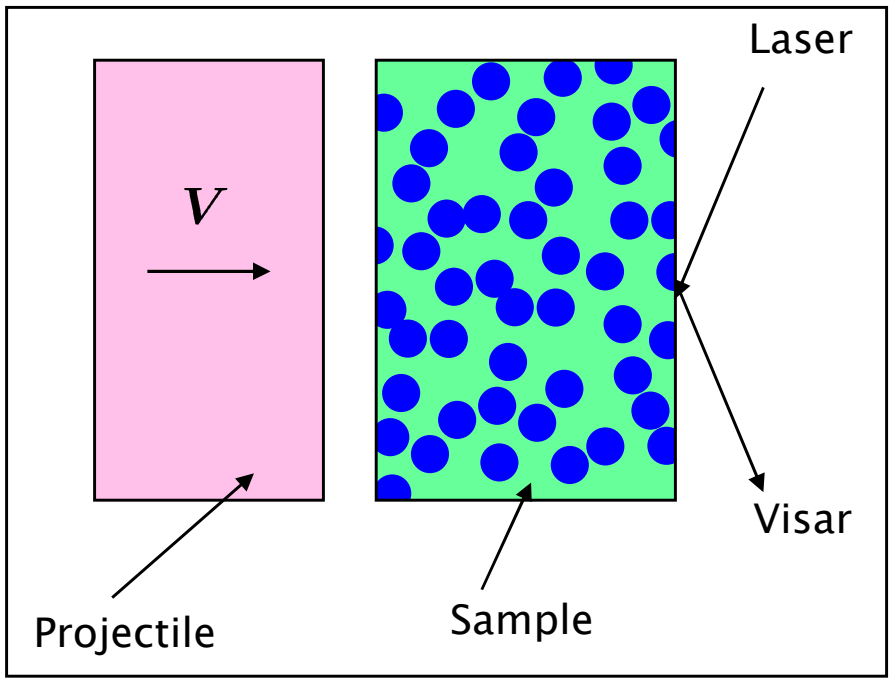

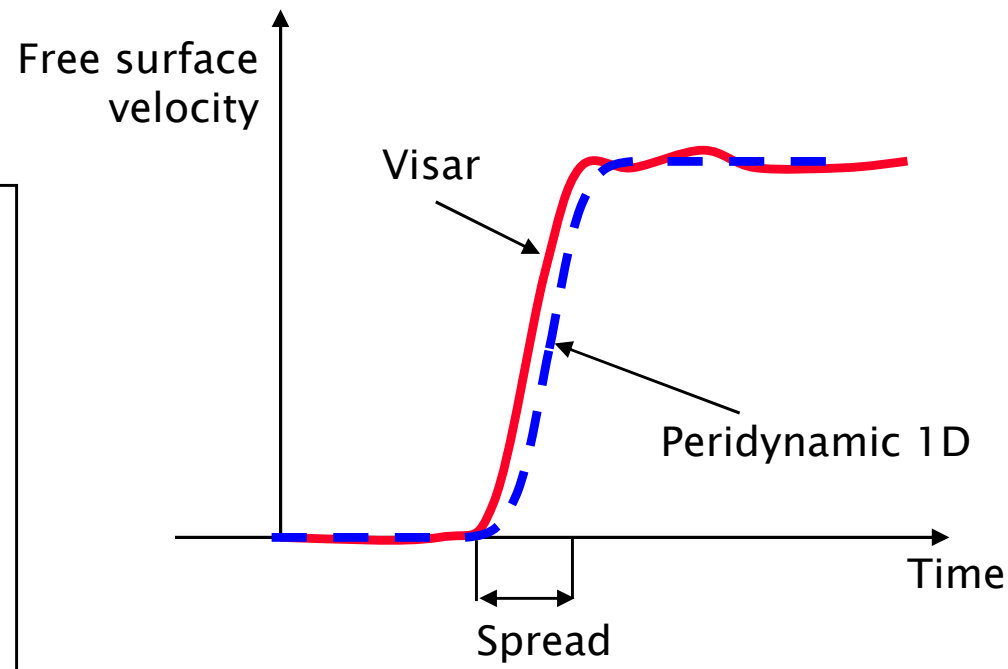

Local model would predict zero spread.

Sandia National Laboratories

Outline

- Objective
- Theory
- EMU numerical method
- Examples
- Heterogeneity and nonlocality
- Fragmentation

Fragmentation example: Expanding brittle tube

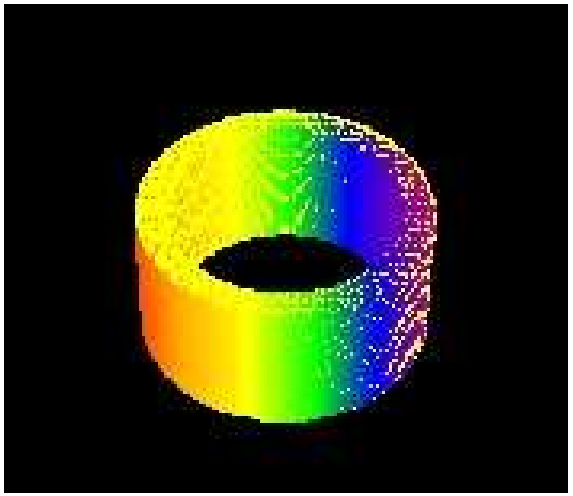

- Outer radius = 100 mm
- Thickness = 10 mm
- Radial velocity = 600 m/s

For each choice of the horizon, select the material model parameters such that the energy release rate is the same for all.

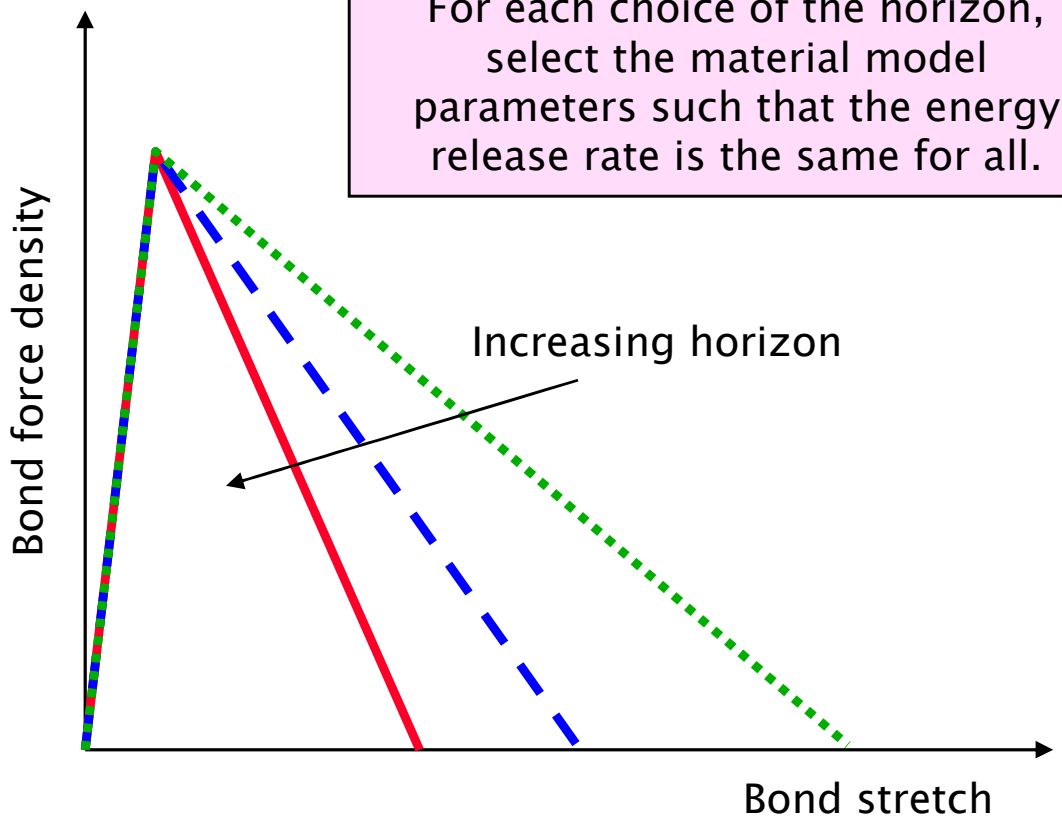

- Grid contains 1% random perturbations to act as seed.

Sandia National Laboratories

Fragmentation example:
Same problem with 4 different grid spacings

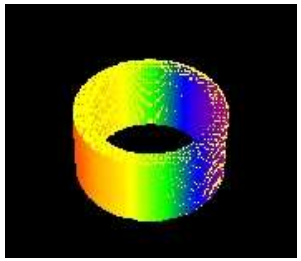

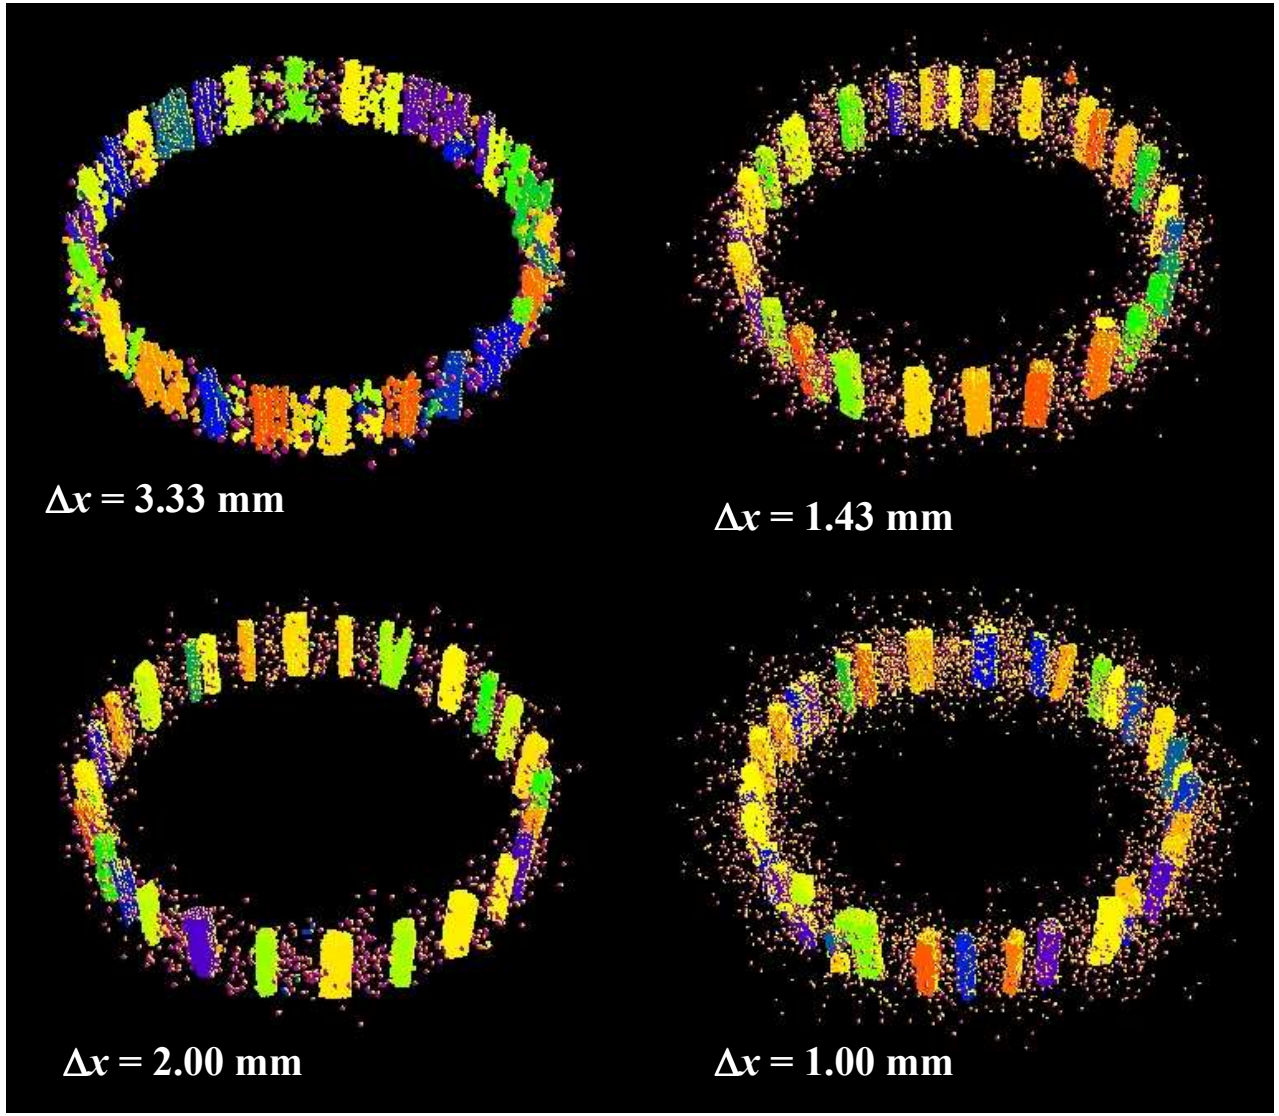

$$\delta = 3\Delta x$$

Colors are just for visualization

Sandia National Laboratories

Fragmentation example: Fragment mass distribution

Cumulative distribution function for 4 grid spacings

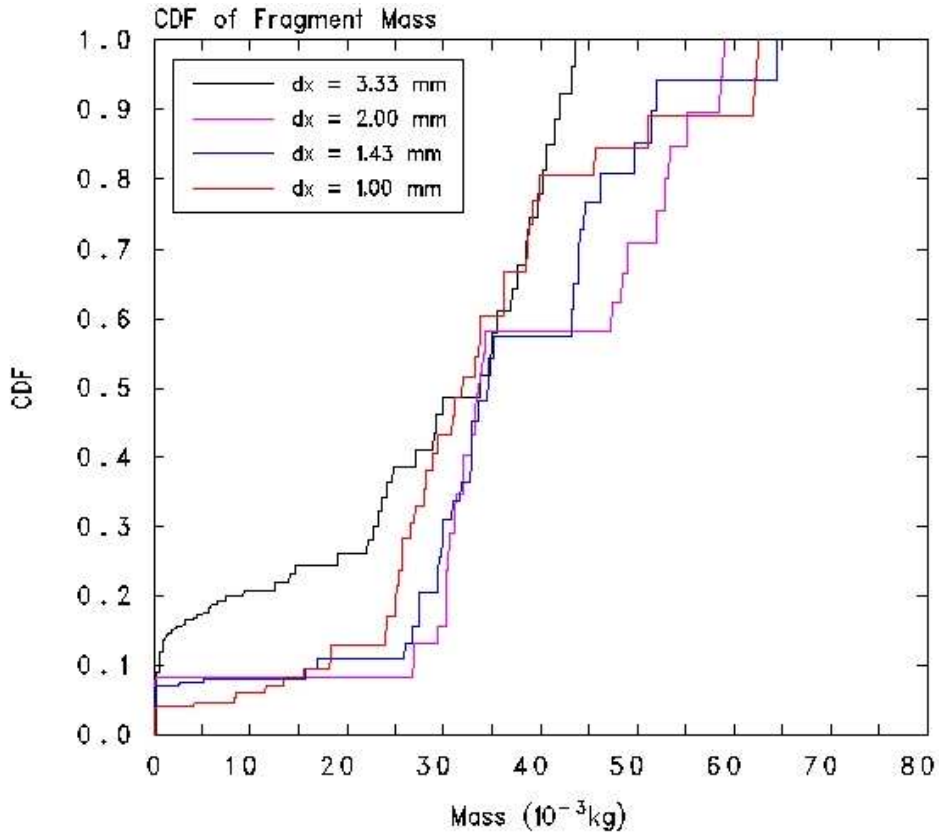

Δx (mm)	Mean fragment mass (g)
3.33	27.1
2.00	37.8
1.43	35.9
1.00	33.5

Sandia National Laboratories

Fragmentation example: Lower initial velocity

- 200 m/s initial radial velocity.
- Not all cracks grow to completion.

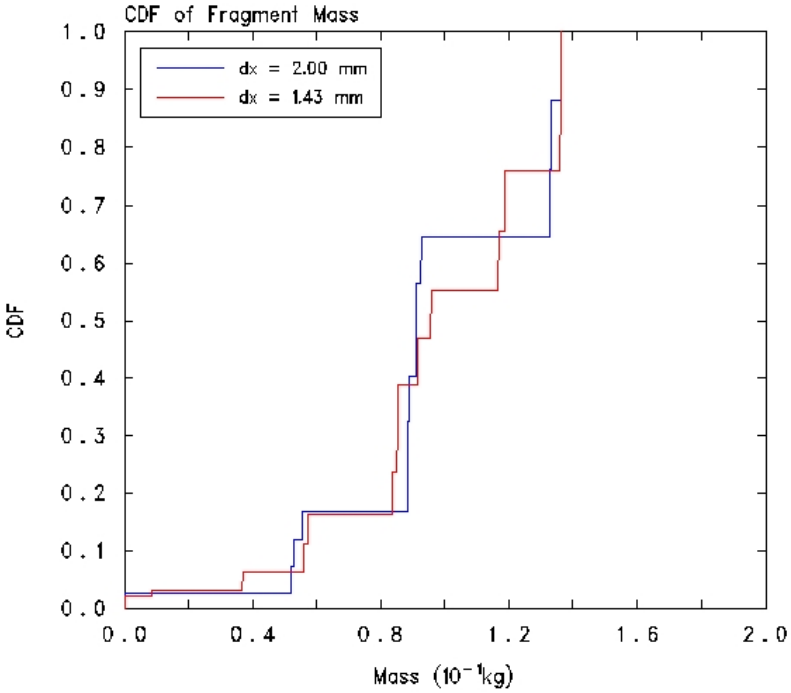

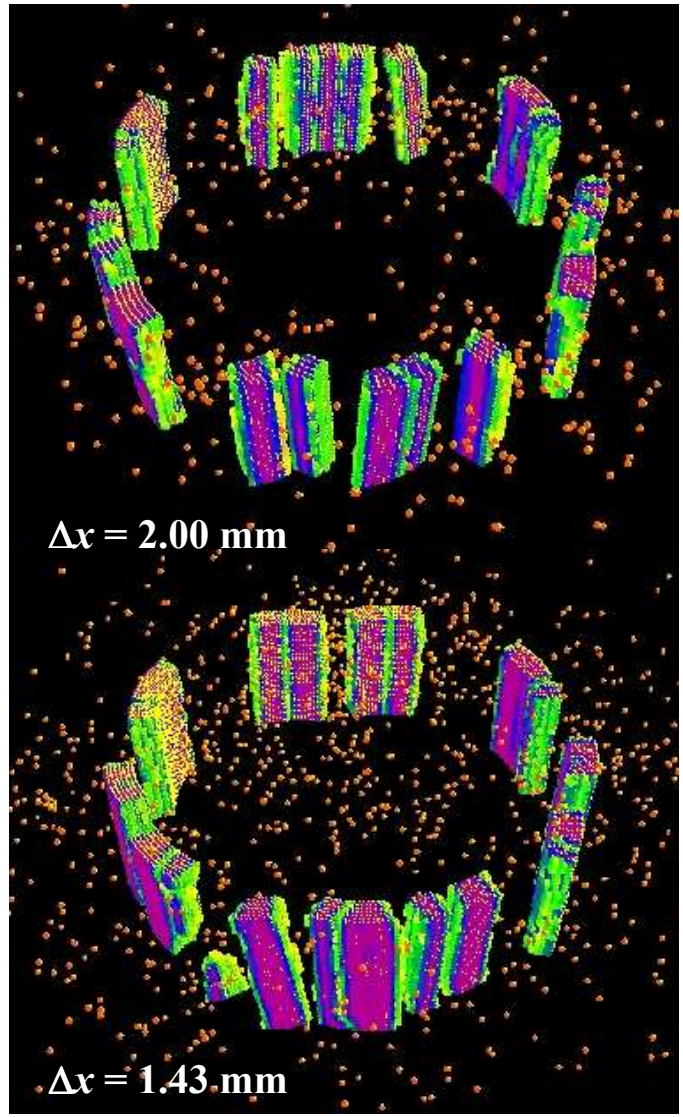

Contours of damage

Sandia National Laboratories

Applications: Fragmentation of a concrete sphere

- 15cm diameter concrete sphere against a rigid plate, 32.4 m/s.
  - Mean fragment size agrees well with experimental data of Tomas.

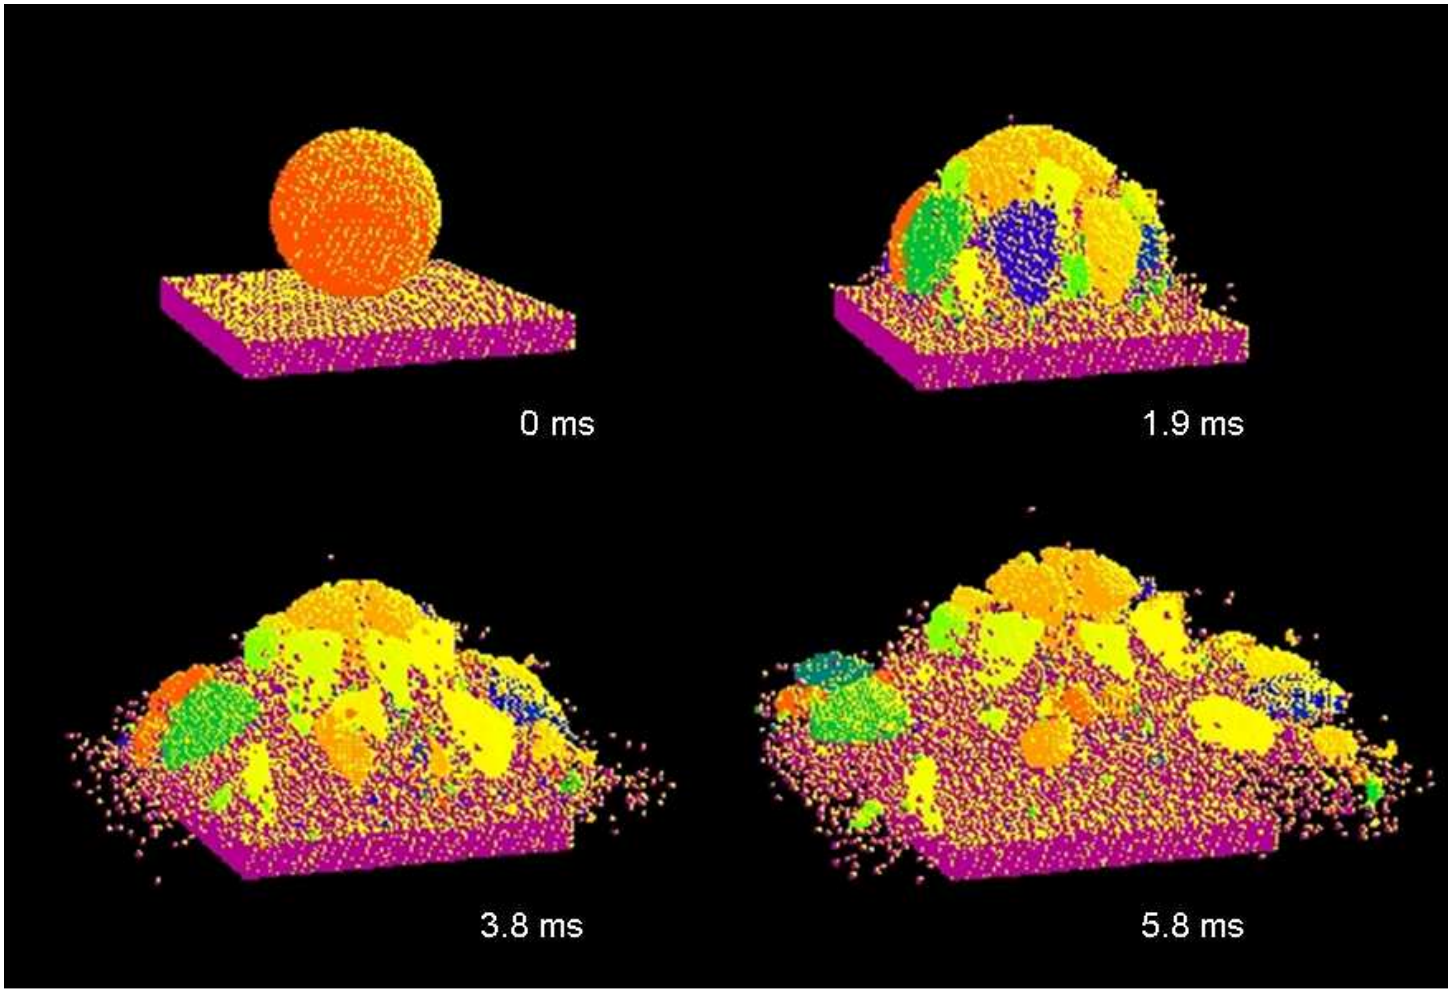

Sandia National Laboratories

Conclusions

- The ability to apply exactly the same equations everywhere yields practical benefits:
  - Cracks nucleate spontaneously.
  - Cracks advance “autonomously” – no need for supplemental equations.
  - Dynamic fracture/fragmentation examples appear to have good convergence properties.

- The theory converges to the classical theory in the limit of small interaction distance.
  - Yet nonlocality seems to be an essential feature of heterogeneous media.

Sandia National Laboratories